

5-31-1985

Preparation and properties of novel dental adhesives based upon pentaerythritol

Yuan-Yuan Su
New Jersey Institute of Technology

Follow this and additional works at: <https://digitalcommons.njit.edu/theses>

 Part of the [Chemical Engineering Commons](#)

Recommended Citation

Su, Yuan-Yuan, "Preparation and properties of novel dental adhesives based upon pentaerythritol" (1985). *Theses*. 2081.
<https://digitalcommons.njit.edu/theses/2081>

This Thesis is brought to you for free and open access by the Electronic Theses and Dissertations at Digital Commons @ NJIT. It has been accepted for inclusion in Theses by an authorized administrator of Digital Commons @ NJIT. For more information, please contact digitalcommons@njit.edu.

Copyright Warning & Restrictions

The copyright law of the United States (Title 17, United States Code) governs the making of photocopies or other reproductions of copyrighted material.

Under certain conditions specified in the law, libraries and archives are authorized to furnish a photocopy or other reproduction. One of these specified conditions is that the photocopy or reproduction is not to be “used for any purpose other than private study, scholarship, or research.” If a user makes a request for, or later uses, a photocopy or reproduction for purposes in excess of “fair use” that user may be liable for copyright infringement,

This institution reserves the right to refuse to accept a copying order if, in its judgment, fulfillment of the order would involve violation of copyright law.

Please Note: The author retains the copyright while the New Jersey Institute of Technology reserves the right to distribute this thesis or dissertation

Printing note: If you do not wish to print this page, then select “Pages from: first page # to: last page #” on the print dialog screen

The Van Houten library has removed some of the personal information and all signatures from the approval page and biographical sketches of theses and dissertations in order to protect the identity of NJIT graduates and faculty.

ABSTRACT

Title of Thesis: Preparation and Properties of Novel Dental Adhesives Based Upon Pentaerythritol

Yuan-Yuan Su, Master of Science in Chemical Engineering, 1985

Thesis directed by: Professor David S. Kristol

Urethane methacrylates were synthesized from pentaerythritol, TDI, HEMA and four phenolic blocking agents or from hydroxypropyl methacrylate, TDI and two phenolic blocking agents. All the products were characterized by melting point, infrared spectroscopy, NMR spectra, and elemental analysis. The bonding of these materials to dentin slices was also investigated. Such materials are supposed to not only react with the organic constituent of dentin but also polymerized with restorative resin. It was found that bond strength was enhanced by the use of the urethane methacrylates, resulting in best mean bonding strengths of 2400 psi.

**PREPARATION AND PROPERTIES
OF
NOVEL DENTAL ADHESIVES BASED UPON PENTAERYTHRITOL**

**by
YUAN-YUAN SU**

**Thesis submitted to the Faculty of the Graduate School of
the New Jersey Institute of Technology in partial fulfillment
of the requirements for the degree of
Master of Science in Chemical Engineering**

APPROVAL SHEET

Title of Thesis: Preparation and Properties of Novel Dental
Adhesives Based Upon Pentaerythritol

Name of Candidate: Yuan-Yuan Su
Master of Science in Chemical Engineering

Thesis and Abstract Approved: _____

David S. Kristol
Professor of Chemistry
Chemical Engineering &
Chemistry

5/1/85

Date

Richard Parker
Professor of Chemistry
Chemical Engineering &
Chemistry

5/1/85

Date

George Y. Lei
Associate Professor of
Chemistry
Chemical Engineering &
Chemistry

5/1/85

Date

VITA

Name: Yuan-Yuan Su

Permanent adress:

Degree and date to be conferred: M.S. ChE. Eng., 1985

Date of birth:

Place of birth:

Secondary education: Yan-Pin High School, 1973

| Collegiate institutes attended | Dates | Degree | Date of Degree |
|------------------------------------|-----------|--------|----------------|
| New Jersey Institute of Technology | 1983-1985 | M.S. | 1985 |
| Taipei Institute of Technology | 1973-1978 | B.S. | 1978 |

Major: Chemical Engineering

Position held: Research Assistant, N.J.I.T., 1983-1985

ACKNOWLEDGEMENT

I would like to express my indebtedness to professor David Kristol for his invaluable guidance and kind assistances during the course of this thesis. I am very thankful to Mr. David May, Mr. Manuel Montero and Mr. Farhad Forohar for their support and encouragement that made this work possible. Special thanks to Dr. George Lei and Dr. Richard Parker for their final corrections of this thesis.

TABLE OF CONTENTS

| Section | Page |
|---|-------|
| ACKNOWLEDGEMENT ----- | ii |
| LIST OF TABLES ----- | iii-v |
| LIST OF FIGURES ----- | vi |
| I. INTRODUCTION ----- | 1-18 |
| II. EXPERIMENTAL ----- | 19-81 |
| III. RESULTS AND DISCUSSION ----- | 82-90 |
| IV. CONCLUSIONS ----- | 91 |
| APPENDIX A. THE EQUIPMENT SET UP FOR PREPARATION OF THE PENTAERYTHRITOL-TDI ADDUCT ----- | 92 |
| APPENDIX B. THE EQUIPMENT SET UP FOR PREPARATION OF THE HYDROXYHEXYL METHACRYLATE ----- | 93 |
| APPENDIX C. THE STRUCTURE OF TMP-TDI ADDUCT ----- | 94 |
| ABBREVIATIONS ----- | 95 |
| BIBLIOGRAPHY ----- | 96-99 |

LIST OF TABLE

| Table | Page |
|---|------|
| I. Preparation of HPMA-TDI-m-Methoxyphenol --- | 23 |
| II. Preparation of Pentaerythritol-TDI-HEMA-Eugenol ----- | 27 |
| III. Preparation of Pentaerythritol-TDI-HEMA-o-Methoxyphenol ----- | 28 |
| IV. Preparation of Pentaerythritol-TDI-HEMA-o-Chlorophenol ----- | 29 |
| V. Melting Point of The Products ----- | 34 |
| VI. Selected IR Absorption of HPMA-TDI ----- | 35 |
| VII. Selected IR Absorption of HPMA-TDI-p-Cresol ----- | 36 |
| VIII. Selected IR Absorption of HPMA-TDI-m-Methoxyphenol ----- | 37 |
| IX. Selected IR Absorption of Pentaerythritol-TDI ----- | 38 |
| X. Selected IR Absorption of Pentaerythritol-TDI-HEMA-p-Cresol ----- | 39 |
| XI. Selected IR Absorption of Pentaerythritol-TDI-HEMA-Eugenol ----- | 40 |
| XII. Selected IR Absorption of Pentaerythritol-TDI-HEMA-o-Methoxyphenol ----- | 41 |
| XIII. Selected IR Absorption of Pentaerythritol-TDI-HEMA-o-Chlorophenol ----- | 42 |
| XIV. Selected IR Absorption of Hydroxyhexyl-methacrylate ----- | 43 |
| XV. NMR Signals of Hydroxyhexylmethacrylate - | 44 |
| XVI. NMR Signals of HPMA-TDI-p-Cresol ----- | 45 |
| XVII. NMR Signals of HPMA-TDI-m-Methoxyphenol - | 46 |
| XVIII. NMR Signals of Pentaerythritol-TDI ----- | 47 |
| XIX. NMR Signals of Pentaerythritol-TDI-HEMA-p-Cresol ----- | 48 |

| | | |
|---------|--|----|
| XX. | NMR Signals of Pentaerythritol-TDI- HEMA-Eugenol ----- | 49 |
| XXI. | NMR Signals of Pentaerythritol-TDI- HEMA-o-Methoxyphenol ----- | 50 |
| XXII. | NMR Signals of Pentaerythritol-TDI- HEMA-o-Chlorophenol ----- | 51 |
| XXIII. | Elemental Analysis of Hydroxyhexyl- methacrylate ----- | 52 |
| XXIV. | Elemental Analysis of HPMA-TDI-p-Cresol -- | 52 |
| XXV. | Elemental Analysis of HPMA-TDI- m-Methoxyphenol ----- | 52 |
| XXVI. | Elemental Analysis of Pentaerythritol- TDI ----- | 52 |
| XXVII. | Elemental Analysis of Pentaerythritol- TDI-HEMA-p-Cresol ----- | 53 |
| XXVIII. | Elemental Analysis of Pentaerythritol- TDI-HEMA-Eugenol ----- | 53 |
| XXIX. | Elemental Analysis of Pentaerythritol- TDI-HEMA-o-Methoxyphenol ----- | 53 |
| XXX. | Elemental Analysis of Pentaerythritol- TDI-HEMA-o-Chlorophenol ----- | 54 |
| XXXI. | Bonding Strength of Pentaerythritol-TDI- HEMA-p-Cresol ----- | 55 |
| XXXII. | Bonding Strength of Pentaerythritol-TDI- HEMA-p-Cresol ----- | 56 |
| XXXIII. | Bonding Strength of Pentaerythritol-TDI- HEMA-p-Cresol ----- | 57 |
| XXXIV. | Bonding Strength of Pentaerythritol-TDI- HEMA-p-Cresol ----- | 58 |
| XXXV. | Bonding Strength of Pentaerythritol-TDI- HEMA-p-Cresol ----- | 59 |
| XXXVI. | Bonding Strength of Pentaerythritol-TDI- HEMA-p-Cresol ----- | 60 |
| XXXVII. | Bonding strength of Pentaerythritol-TDI- HEMA-o-Methoxyphenol ----- | 61 |

| | | |
|----------|--|----|
| XXXVIII. | Bonding Strength of Pentaerythritol-TDI- HEMA-o-Methoxyphenol ----- | 62 |
| XXXIX. | Bonding Strength of Pentaerythritol-TDI- HEMA-o-Chlorophenol ----- | 63 |
| XXXX. | Bonding strength of Pentaerythritol-TDI- HEMA-o-Chlorophenol ----- | 64 |

LIST OF FIGURES

| Figure | Page |
|---|------|
| 1. IR Spectra of Hydroxyhexylmethacrylate ----- | 65 |
| 2. IR Spectra of HPMA-TDI ----- | 66 |
| 3. IR Spectra of HPMA-TDI-p-Cresol ----- | 67 |
| 4. IR Spectra of HPMA-TDI-m-Methoxyphenol ----- | 68 |
| 5. IR Spectra of Pentaerythritol-TDI ----- | 69 |
| 6. IR Spectra of Pentaerythritol-TDI- HEMA-p-Cresol ----- | 70 |
| 7. IR Spectra of Pentaerythritol-TDI- HEMA-Eugenol ----- | 71 |
| 8. IR Spectra of Pentaerythritol-TDI- HEMA-o-Methoxyphenol ----- | 72 |
| 9. IR Spectra of Pentaerythritol-TDI- HEMA-o-Chlorophenol ----- | 73 |
| 10. NMR Spectra of Hydroxyhexylmethacrylate ----- | 74 |
| 11. NMR Spectra of HPMA-TDI-p-Cresol ----- | 75 |
| 12. NMR Spectra of HPMA-TDI-m-Methoxyphenol ----- | 76 |
| 13. NMR Spectra of Pentaerythritol-TDI ----- | 77 |
| 14. NMR Spectra of Pentaerythritol-TDI- HEMA-p-Cresol ----- | 78 |
| 15. NMR Spectra of Pentaerythritol-TDI- HEMA-Eugenol ----- | 79 |
| 16. NMR Spectra of Pentaerythritol-TDI- HEMA-o-Methoxyphenol ----- | 80 |
| 17. NMR Spectra of Pentaerythritol-TDI- HEMA-o-Chlorophenol ----- | 81 |

Introduction

I. Introduction : For more than a quarter of century, many investigators¹⁻¹⁵ have sought to obtain the bonding of restorative resin to dentin by means of an intermediary monomer. Although the acid-etch technique was introduced for the bonding of resins to enamel for the prevention of pit and fissure caries,⁶⁻⁷ this technique does not give adequate bond strengths to the dentin surface. Further, the use of hypertonic solutions of phosphoric or citric acid on vital dentin is usually contraindicated because they can have harmful effects on the dental pulp.⁸⁻⁹ Attempts to bond through a micromechanical mechanism by an enzymatic pretreatment have also been made.¹⁰⁻¹⁵ For example, it was thought that limited treatment of the dentin with collagenase will cause pitting and result in greater surface contact with adhesive agents. However, these attempts were unsuccessful.

¹⁶One approach which had limited success was the use of bifunctional monomers, in which one part of the monomer molecule was designed to have a potential capability to react with either the inorganic or the organic constituent of the dentin, while another part of the molecule containing a polymerizable double bond caused a polymerization reaction with restorative resins. These monomers were 2,4-tolylene diisocyanate reacted with 2-hydroxyethyl methacrylate at one isocyanate. However, such monomers which might possibly react with the -OH or -NH₂ side chains of the dentin protein were found to give relatively low bonding strength. It was


suggested that this result might be associated with the presence of water, which probably reacts with the free isocyanate in the bifunctional monomer, more readily than does with collagen. In order to avoid the reaction between isocyanate groups and water from occurring, our laboratory conceived the idea of the blocked isocyanates which were prepared by subsequent treatment of the second isocyanate group with phenols. Thus, the object of this research is to prepare, characterize and test bifunctional monomers containing blocked isocyanate groups for their ability to form chemical bonds to human dentin.

II. Principle

A. The Development of Adhesive Material : The human tooth basically consists of the crown and root. The crown is covered by a thin coating of enamel, while the root contains a coating called cementum. Beneath the enamel, which is the hardest substance in the human body and has no blood supply, is the composite dentin containing 60% hydroxyapatite, 20% organic matter and 20% water by weight. Organic matter called collagen¹⁷⁻¹⁸ is a triply stranded protein molecule which contains a large number of polar groups with active hydrogen such as -NH_2 , -OH , -COOH . In addition, the primary amide groups ($\text{-NH}-\overset{\text{O}}{\underset{\text{||}}{\text{C}}}-$) present in the backbone of collagen have much less active hydrogens.

The well-known reactions of organic isocyanates with active hydrogen compounds¹⁹⁻²⁰ and the potential availability of a large number of such active hydrogen sites in collagen


suggested the synthesis of monomers with isocyanate groups as potential adhesion-promoting agents for collagenous substrates. The chemical mechanism for promoting adhesion to dentin via the isocyanate group is as follows:

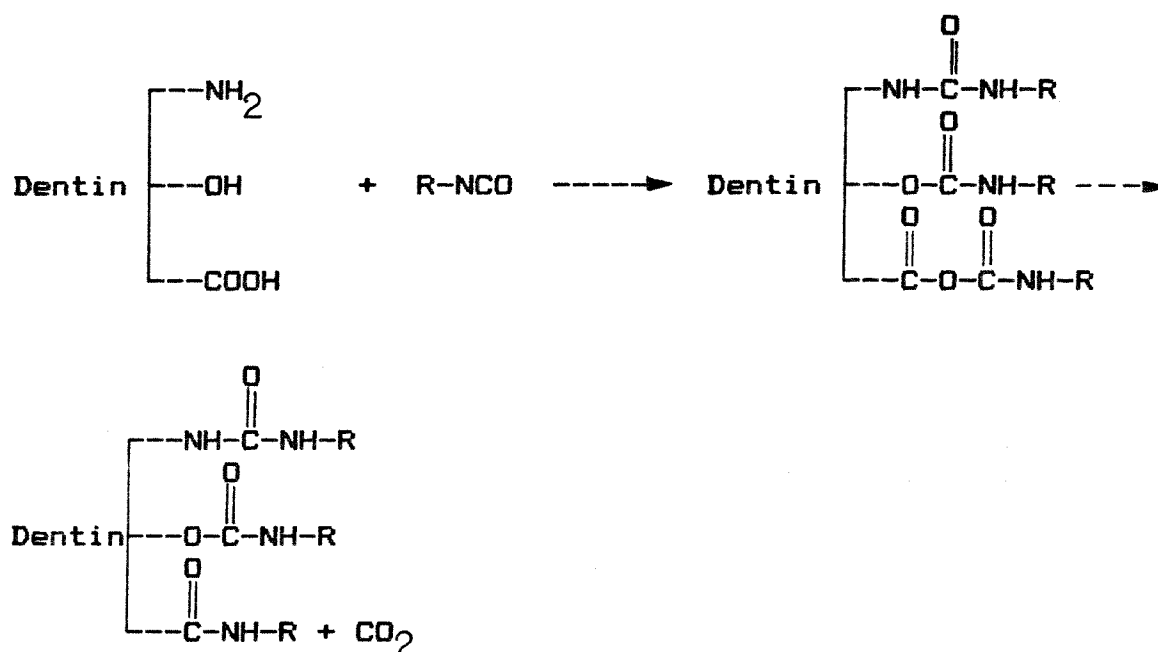

In an oral environment, however, the competitive reaction of water present on the dentin surface with isocyanate can be significant.



The amine group formed after the release of carbon dioxide can react with another isocyanate to form urea linkage,



That means one water molecule can consume two isocyanate groups that are available for bonding to the dentin surface. Furthermore, carbon dioxide produced in the water-isocyanate reaction tends to form gas bubbles which will foam the

adhesive material and restorative material, possibly also resulting in the reduction of bonding strength.²¹ Fortunately, Wick²² described that one of the distinct advantages of blocked isocyanates is that they do not react with water at neutral PH at ambient temperature. In this way, it makes possible to develop a covalent bonding of the polymeric adhesive to dentin by reacting the blocked isocyanate functions to the hydroxyl or amino groups of collagen. The mechanism of the reaction along with the release of the blocking agent, R'-OH




B. General Chemistry of Blocked Isocyanate : A blocked isocyanate²³ is an isocyanate which has been reacted with a material which will prevent its reaction at room temperature, with compounds that conventionally react with isocyanates but will permit that reaction to occur at higher temperature. The formation mechanism of a blocked isocyanate is




Where BH is a hydrogen donor molecule such as alcohol, phenol or amine.

The overall reaction with active hydrogen compounds is

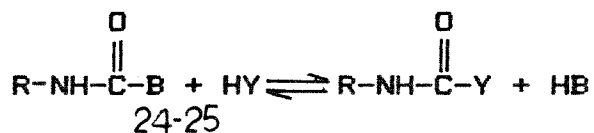



Williams has studied the alcoholysis of phenyl N-phenyl urethanes and concluded that the mechanism of the deblocking reaction is an E1cB type involving two intermediates :



BH: Blocking Agents

Thus, the initial step is proton removal in a rapid equilibrium reaction followed by the slower expulsion of the phenolate or alkoxide ion.

²⁶
Rand has found that the course of the transesterification reactions is a rapid deblocking reaction to phenol (BH) and free isocyanate followed by a slower, rate-controlling reaction of the isocyanate with the alcohol (ROH).



In contrast to the situation with alcohol, the reaction between a blocked isocyanate and primary or secondary amines is relatively rapid and not readily reversible. The rate-controlling step was the deblocking of the urethane to isocyanate, followed by the rapid reaction with the amine. It can be concluded that the free isocyanate site will largely react with NH_2 groups on the surface of dentin instead of OH groups.

C. Dissociation of blocked isocyanate : It can be assumed that the bonding strength of the adhesive material to dentin is mainly dependent on the number of free isocyanate sites which are available to react with amine groups in dentin. Thus, the rate and extent of the deblocking reaction are significant and, therefore, described in this section.

Due to its importance in industrial applications, several investigators have studied the deblocking reaction

for many years. Wicks²² has summarized that the rate and extent of the deblocking reaction are affected by structure of blocking agents, catalyst, and solvent. Among the above three factors the choice of a compound to be used as a blocking agent is particularly crucial to the successful use of a blocked isocyanate. Frisch's²⁶ study showed that the thermal deblocking reaction of urethane in very general terms proceeds in the following order:

| | |
|-------------------|-------|
| Alkyl-NHCOO-Alkyl | 250°C |
| Aryl-NHCOO-Alkyl | 200°C |
| Alkyl-NHCOO-Aryl | 180°C |
| Aryl-NHCOO-Aryl | 120°C |





It was recognized that urethane derived from alkyl groups were more stable than those derived from aryl groups. Moreover, Fedoseev²⁷ reported that the stability of blocked isocyanates is significantly affected by substitution on the aromatic ring. The presence of electron-withdrawing groups decreases stability, and that of electron-releasing groups increases stability. Moreover, Ortho-substituted phenol will tend to deblock at lower temperatures than para-substituted ones.²⁸⁻³⁰ According to the above guidelines, Kanaya tried p-cresol, while Chikazoe and Yamamoto tried phenol as blocking agents in their work. The choice of p-cresol, eugenol, ortho-methoxyphenol, and ortho-chlorophenol in this study are primarily based on a previous study by Dr. W.H. Snyder, Dr. D. Kristol, and colleagues.³¹⁻³³

Like most reactions, catalyst also plays an important

role in deblocking reactions. The deblocking temperature can be largely lowered by means of introducing a catalyst to the deblocking reaction. A patent³⁴ claims that calcium 2-ethyl-hexanoate is significantly more effective as a catalyst than tin compound. Also claimed are Mg, Ca, Sr, or Ba salts of hexanoic, octanoic, naphthenic or linoleic acid. Another patent³⁵ claims a marked synergistic effect with a combination of organotin compounds and quaternary ammonium salts, with not only a lower "release temperature" but also improved heat stability of the cured urethane coatings. Thus the combination of dibutyltin dilaurate and an alkyl (C_{11} - C_{18}) dimethyl benzyl ammonium phthalimide largely decreased the "release temperature". For the effect of solvent, Fedoseev²⁶ and co-workers studied the deblocking reaction in a series of solvent and found that the reaction rate increased with solvent polarity. Reilly and Orchin³⁶ showed that dissociation proceeded more rapidly at 60°C in tetrahydrofuran than in benzene at 80°C.


D. Reaction of Isocyanates : In most reactions, especially with active hydrogen compounds, the aromatic isocyanates are more reactive than the aliphatic isocyanates. In addition, substitution of electronegative groups on the aromatic ring enhances the reactivity whereas electropositive groups reduce the reactivity of the isocyanate. As would be expected, steric hindrance on either the isocyanate or the active hydrogen compound will retard the reaction. All of the reactions are subject to catalysis by acid and, usually


most strongly, by base. Typical reactions of isocyanates with active hydrogen compounds are shown as follows:³⁷

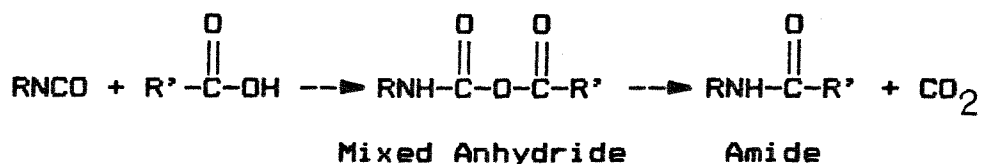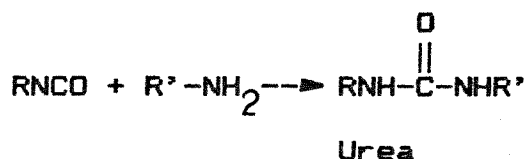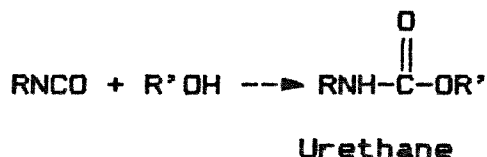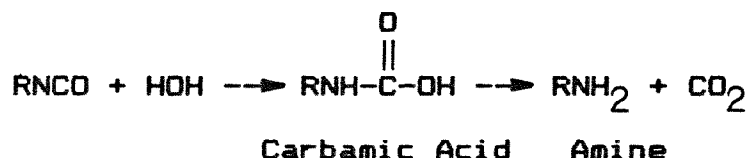

The usual order of reactivity is $\text{R}'\text{NH}_2 > \text{R}'\text{OH} > \text{HOH} > \text{C}_6\text{H}_5\text{OH} > \text{R}'\text{COOH}$. These reactions are considered to be the backbone of the polyurethane chemistry.

It is important to note that the further reaction between the primary product with an active hydrogen atom and another isocyanate group may also take place as follows:

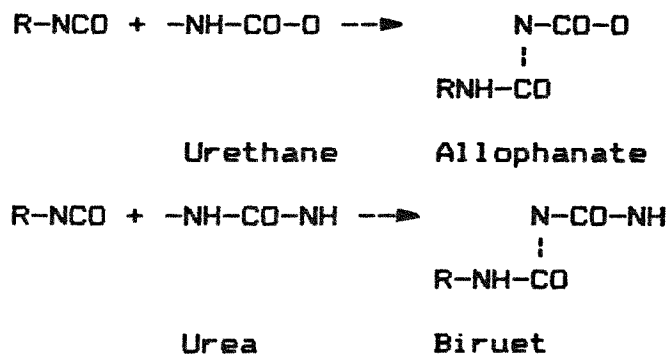





Amide Acyl Urea

³⁷ These reactions do not occur appreciably unless the reactant are heated or unless there is a catalyst present which will encourage the reaction. Some times these secondary reactions are desired for the formations of crosslinking and branching which have an effect on polyurethane properties.


As a special case of the reaction with unsaturated compounds, isocyanates may react with themselves to form dimers, trimers, and even linear polymers.³⁷

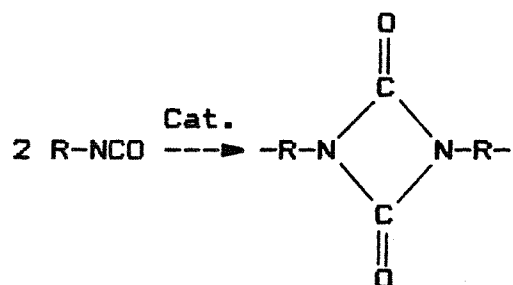

Isocyanate Dimer

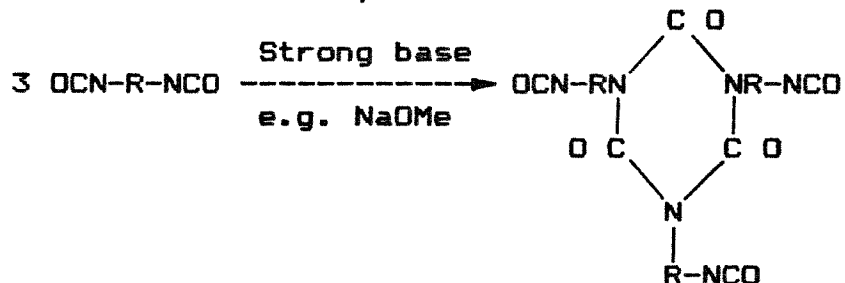

Isocyanate Trimer

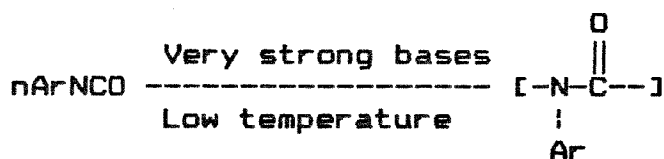


Linear Polymer

Isocyanate dimers at elevated temperatures react much as do isocyanates, sometimes by prior dissociation to the isocyanate, sometimes by direct reaction between dimer and active hydrogen compound. Thus, dimers may give nearly the same reaction as the monomeric isocyanate. Trimerization is an important reaction in urethane polymer chemistry in that the trimer is relatively quite stable. In addition, trimerization is significant because it leads to branching of the polymer. For the linear polymer, its properties resemble nylon. So it is of importance in fiber industry.

E. Polymerization reaction: As noted before, the bifunctional monomers expected to come out of this study should both bond to the surface of the dentin and also polymerize with the restorative material. Currently, the most widely used restorative material is acrylic resin, poly methyl methacrylate.³⁸ In molding procedures, however, poly methyl methacrylate by itself is not used in dentistry to a great extent. Rather, the liquid monomer, methyl methacrylate, is mixed with the polymer at a ratio of 70% to 30% by weight. The monomer partially dissolves the polymer to form a plastic dough. this dough is packed into the mold, and the monomers are polymerized.

When the dough of MMA-PMMA is placed on the adhesive material, the polymerization reaction occurs not only between methyl methacrylate monomers themselves but also between methyl methacrylate monomers and 2-hydroxy ethyl methacrylates. The concept of dental adhesion by means of


diisocyanates can be generalized in the following Chemistry Scheme :

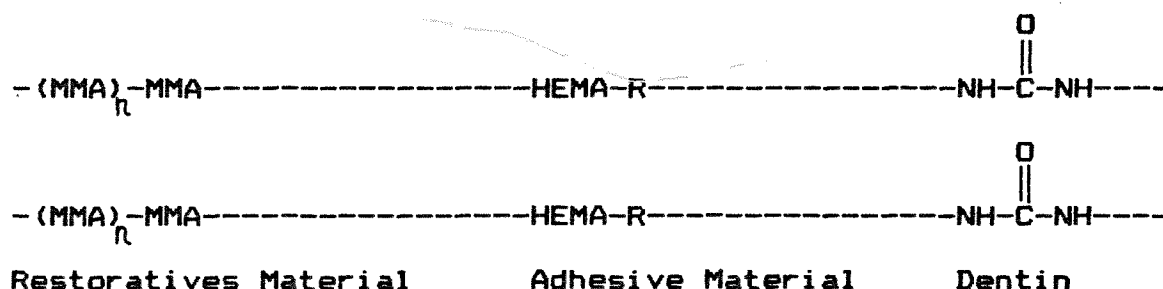

In this way it can be recognized that the interface of restorative material layer and adhesive material layer is a copolymer, and the restorative material layer itself is a homopolymer. Both of these reaction products are derived from vinyl radical polymerizations. The general chemistry for both homopolymerization and copolymerization will be discussed separately as follows:

39


F. Free radical Homopolymerization: Initiation in the presence of an initiator, I, may be considered in two steps: first, the rate-determining decomposition of the initiator into free radicals, R \cdot ,




and, second, the addition of a monomer unit to form a chain radical M $_1\cdot$



The successive steps in propagation,

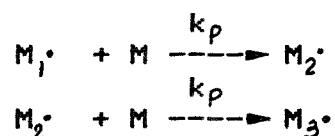


or, in general



are assumed all to have the same rate constant K_p because radical reactivity is presumed to be independent of chain length.

The termination step involves combination



or disproportionation, where M_X and M_Y are alkane and alkene.



Only in the case where it is necessary to distinguish between the two mechanisms, the termination rate constant can be denoted K_t , a lumped parameter.

The rate of initiation is

$$V_i = \left(\frac{d [M^\bullet]}{dt} \right)_i = 2 f k_d [I]$$

where f = efficiency of the radical to initiate the monomer

The rate of termination is

$$V_t = - \left(\frac{d [M^\bullet]}{dt} \right)_t = 2 k_t [M^\bullet]^2$$

At the steady-state, $V_i = V_t$


$$[M^\bullet] = \left(\frac{f k_d [I]}{k_t} \right)^{1/2}$$


The rate of propagation,

$$V_p = - \frac{d [M]}{dt} = k_p [M] [M^\bullet] = k_p \left(\frac{f k_d [I]}{k_t} \right)^{1/2} [M]$$

Thus the over-all rate of polymerization should be proportional to the square root of the initiator concentration and to the first power of the monomer concentration. A number of substances which are capable of generating free radicals are potent initiators for the preparation of poly methyl methacrylate resins. The most commonly employed is benzoyl peroxide, which decomposes at relatively low temperature to release free radicals. In order to obtain good physical properties, a maximal useful concentration of the peroxide is 2.0 percent.⁴⁰ Hence, aside from increasing the concentration of monomer and initiator, the only way to increase the rate of polymerization is to find a good promoter which can activate the peroxide to decompose faster. This permits an increase in the rate of polymerization by increasing f , the efficiency of the radical, without increasing the initiator concentration. Meltzer and Tobolsky⁴¹ showed that the propagation steps and termination steps of the chain reaction are not affected by a promoter in a peroxide-amine initiated system. It must, therefore, change the initiation step.

Steven's⁴² work showed the decomposition step mechanism of initiator as follows:

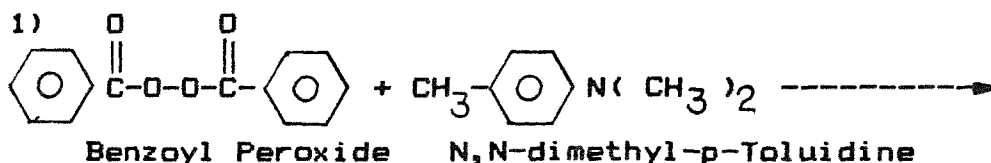

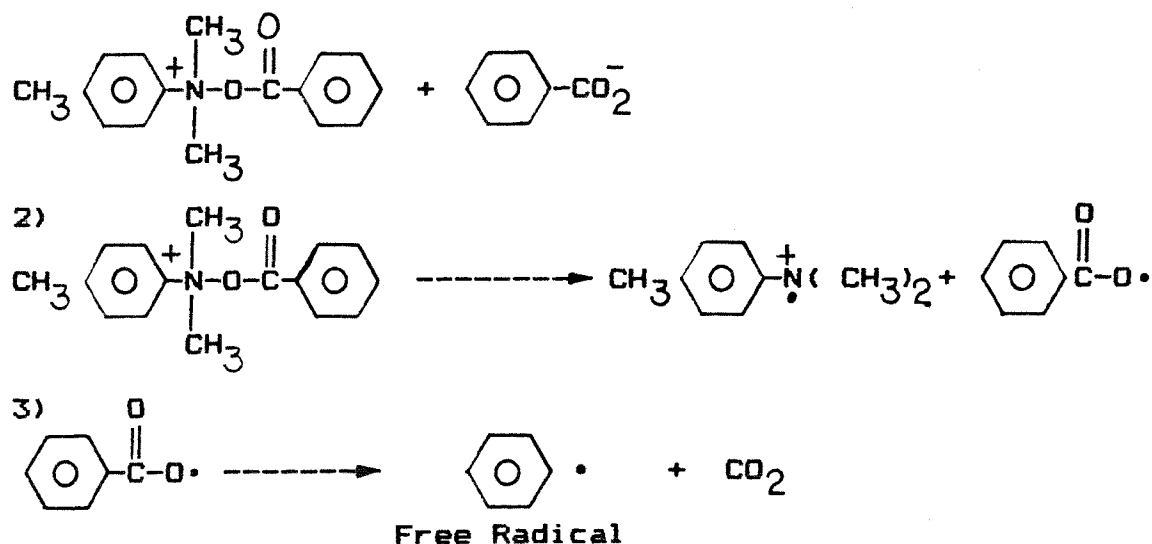


According to the above decomposition mechanism, the substitution of electron-repelling groups⁴³ in the para position of dimethylaniline will increase decomposition rate efficiency. But a methyl group substitution⁴³ in ortho position of dimethylaniline reduces the decomposition rate of benzoyl peroxide to such an extent that polymerization does not take place readily. As compared to the meta position, an aliphatic group in ortho position decreases peroxide decomposition. By using a modified ultrasonic viscometer, Brauer⁴³ and his coworkers concluded that polymerization with tertiary aromatic amines proceeds fastest. Furthermore, they showed that polymerization with N,N-dimethyl-p-toluidine or 2,2'-(m-tolylimino) diethanol gave products having the best physical properties. For the consideration of physical properties of material, however, a maximal useful concentration of the amine was found to be approximately 0.75 percent.³⁸

³⁰
G. Copolymerization of Methyl Methacrylate and Hydroxyethyl Methacrylate : The initiation and termination steps are the

44

same as previously mentioned in homopolymerization. Dostal made the first attack on the mechanism of copolymerization by assuming that the rate of addition of monomer to a growing free radical depends only on the nature of the end group on the radical chain. Thus monomers M_1 and M_2 lead to radical of types M_1^\cdot and M_2^\cdot . There are four possible ways in which monomer can add:

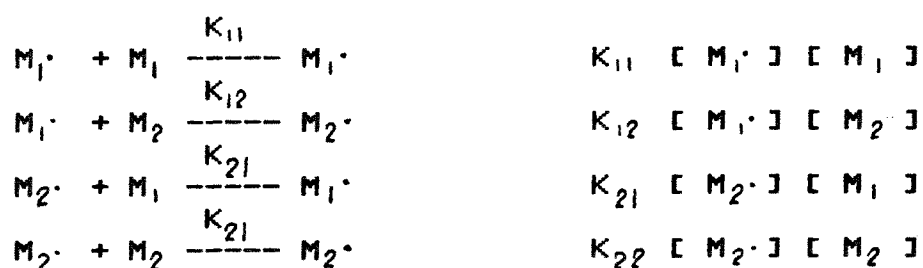

If we assume that a steady state applies to each radical type separately,⁴⁵⁻⁴⁸

$$K_{21} [M_2^\cdot] [M_1] = K_{12} [M_1^\cdot] [M_2]$$

$$-\frac{d[M_1]}{dt} = K_{11} [M_1^\cdot] [M_1] + K_{21} [M_2^\cdot] [M_1]$$

$$-\frac{d[M_2]}{dt} = K_{12} [M_1^\cdot] [M_2] + K_{22} [M_2^\cdot] [M_2]$$

$$\frac{d[M_1]}{d[M_2]} = \frac{[M_1]}{[M_2]} \frac{r_1 [M_1] + [M_2]}{[M_2] [M_1] + r_2 [M_2]}$$

$$r_1 = K_{11} / K_{12} \quad r_2 = K_{22} / K_{21}$$

M_1 : Methyl Methacrylate monomer

M_2 : Hydroxyethyl Methacrylate monomer

M_1^\cdot : living copolymer with Methyl Methacrylate terminers

M_2^\cdot : living copolymer with Hydroxyethyl Methacrylate terminers

$$1) \text{ If } r_1 \cdot r_2 = 1 \quad \text{then} \quad \frac{d[M_1]}{d[M_2]} = r_1 \frac{[M_1]}{[M_2]}$$

In this case the end group on a growing chain has no influence on the rate of addition, and the two types of units are arranged at random along the chain in relative amounts determined by the composition of the feed and the relative reactivities of the two monomers. This copolymer system is said to be ideal.


$$2) \text{ If } r_1 = r_2 = 0, \quad \text{then} \quad \frac{d[M_1]}{d[M_2]} = 1$$

The monomers alternate regularly along the chain regardless of the composition of the monomer feed. This is so called alternative copolymer.

3) If $r_1, r_2 > 1$, The system corresponds to the tendency to form block copolymer.


Most actual cases lie between the ideal and the alternating systems; $0 < r_1, r_2 < 1$.

H. Effects of Cross Linking on Dental Material: Theoretically, cross-linkage⁴⁹ provides a sufficient number of bridges between the linear macromolecules to form a three-dimensional network that alters the strength, solubility, and water sorption of the resin. A general cross linking structure is as follow :

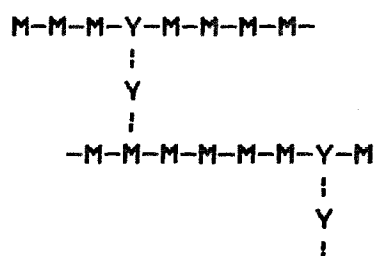

Most acrylic resin materials contain a cross-linking

agent such as ethylene glycol dimethacrylate :

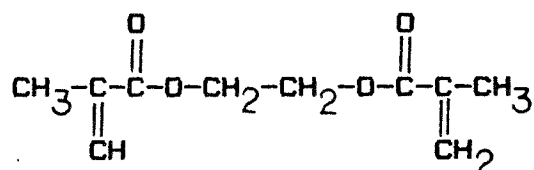

This chemical contains two polymerizable bonds, and it can cross-link with other groups in at least two directions when it is polymerized. When it is used as a copolymer with methyl methacrylate, a more insoluble and infusible resin results compared with the similar properties of poly methyl methacrylate alone.

For the investigation of the mechanical properties, investigations have been carried out in Japan by Masuhara and Hirasawa⁵⁰ which included the study of hardness, tensile and transverse strengths, abrasion resistance and water absorption of co-polymers of methyl methacrylate and a variety of cross-linking agents. Their results indicated that there was a small increase in tensile strength in some of the cross-linking specimens over that of linear polymethyl methacrylate ones. All other tests displayed no significant difference.

I. Residual Monomer in Restorative Resins: Since the introduction of restorative homopolymerizing resins there has been a continuous effort to improve the properties of the material and the quality of the finished restoration. The shortcomings of resin restorations have been discussed fully and are well known. Some of the difficulties encountered in the past were the lack of color stability,

poor adaption, low strength and hardness, and an absence of anticarcinogenic characteristics. Investigations of the mechanical properties of resins have indicated that they are related, in general, to the residual monomer content. The modulus of elasticity, yield strength and hardness develop with time, and the rate of improvement exhibit a direct relationship to the decrease in the monomer content.⁵¹⁻⁵² Generally, the more rapidly the residual monomer is reduced, the more rapidly the physical properties improve.

Our work is an attempt to improve the mechanical properties of methacrylate-based dental restorative resins.

EXPERIMENTAL

I. Synthesis

A. HPMA-TDI-Blocking Agent Synthesis

1. Preparation of HPMA-TDI Adduct: This reaction was carried out in a solution which contains TDI (2,4-toluene diisocyanate) and HPMA (2-hydroxy propyl methacrylate) in the molar ratio 3:1. The apparatus was set up as indicated in Appendix A.

120.0 grams (0.690 moles) of TDI was stirred with 500 mL of petroleum ether and 6 drops of DBTDL (dibutyltin dilaurate) as catalyst in a high shear stirring flask. The mixing was carried out for 15 minutes in a nitrogen atmosphere. HPMA, 33.0 grams (0.230 moles) was added dropwise to the solution by means of an addition funnel.

Under conditions of vigorous agitation and nitrogen circulation, the reaction was exothermic. A cooling water bath was used to maintain the temperature below 35°C to prevent gel formation due to by-product reactions.

After one hour addition of HPMA, 250 mL of petroleum ether was added. Addition of fresh petroleum ether should turn the reacting solution cloudy. If this does not occur, the agitation is continued and the rate of HPMA is controlled until the desired cloudiness is obtained. Generally, the rate of HPMA is controlled at 1 drop/15 secs. The addition of fresh petroleum ether can also prevent HPMA-TDI adduct from sticking to the body of the flask. Therefore, it is necessary to keep adding fresh petroleum ether during

the reaction. The total amount of fresh petroleum ether being added in the adducting reaction should not be less than 1000 mL.

After all the HPMA has been added, the reaction was allowed to proceed overnight under conditions of continuous agitation and nitrogen atmosphere.

2. Precipitation of HPMA-TDI Adduct: The stirrer was turned off, 100 mL of petroleum ether was added and the system was left undisturbed under nitrogen circulation for at least 6 hours. The colorless liquid at the top of the flask consisting of excess TDI and petroleum ether was suctioned off by means of a rubber bulb.

Another 1000 mL of fresh petroleum ether was added and the solution was continuously stirred for 20 minutes in order to remove the TDI residues adsorbed on HPMA-TDI adduct. This purification process was repeated twice more. Finally, the solid product at the bottom of the flask was collected by suction filtration. The filtered cake was washed with fresh petroleum ether to ensure the complete removal of TDI residues. The filtered cake was placed on a watch glass and vacuum dried at room temperature for one day to remove all traces of petroleum ether from the adducting product. A yield of 30 grams (41%) of HPMA-TDI adduct was obtained.

3. Blocking HPMA-TDI Adduct: The HPMA-TDI adduct from part 2 of section A was blocked with two blocking agents such as p-cresol, and m-methoxy phenol. However, in this section only the blocking reaction of p-cresol will be discussed in

detail. For the case where m-methoxyphenol is used as a blocking agent, the experimental procedure used is similar to the one discussed for p-cresol. Reaction conditions, such as required time for completion of the blocking reaction, amount of blocking agent, etc., are listed in Table I

12.0 grams (0.038 moles) of the HPMA-TDI adduct were dissolved in 150 mL of dry THF (tetrahydrofuran) in a 250 mL Erlenmeyer flask. [one liter of THF solvent had been dried by the addition of lithium aluminum hydride, and a simple distillation of the resulting suspension was performed.] 5 drops of DBTDL as catalyst was added to the solution along with 4.9 grams (0.045 moles, 20% excess) of p-cresol. The solution was gently shaken to ensure that all reactants were mixed well and nitrogen gas was passed through it for about 1 to 2 minutes. The flask was now capped with a rubber stopper, which was wrapped in aluminum foil to prevent direct contact with the blocking solution. The blocking reaction was carried out in a hot oil bath maintained at 50°C. A sample was checked for a free isocyanate peak at 2250 cm^{-1} by means of an infrared spectrophotometer. For the case of p-cresol, it took three days for the completion of the blocking reaction, as shown by the absence of a free isocyanate peak. The solution at this point became more viscous and its color changed from light to dark yellow.

4. The Precipitation of P-cresol Blocked HPMA-TDI Adduct:

The blocked solution from part 3 of section A was filtered to remove undissolved impurities. Before the precipitation

was performed, it was necessary to ensure that each drop of the blocked solution added to petroleum ether immediately precipitated as a fine solid material. Formation of large coalesced particles on contact of the blocked solution with petroleum ether would imply that the blocked solution had to be diluted with more dry THF solvent. On the other hand, too much dilution with dry THF solvent would cause the formation of a cloudy solution instead of fine powder precipitation and loss of product. A total of 100 mL of dry THF was added to the solution of HPMA-TDI-p-cresol and the contents of the flask was shaken gently. The diluted blocked solution was added dropwise to 1000 mL of petroleum ether in a flask under nitrogen atmosphere and vigorous agitation. Upon contact of the blocked HPMA-TDI solution with the petroleum ether, a well dispersed white solid was observed. After the addition of about half the blocked solution, 500 mL of petroleum ether was poured into the solution to prevent the precipitate from coalescing to each other or from sticking to the wall of flask. Once all the blocked HPMA-TDI solution was precipitated, the excess p-cresol, dry THF, and catalyst were removed by washing with petroleum ether. The washing procedure described in part 2 of section A would be applicable to the above case. Finally, 13.0 grams (81% yield) of HPMA-TDI-p-cresol blocked adduct was obtained.

Table I Preparation of HPMA-TDI-m-methoxyphenol

The general procedure is the same that was described in parts 3,4 of section A with following quantities of the reactants and characteristics:

Weight of the HPMA-TDI Adduct : 14.0 grams (0.044moles)

THF solvent used in the blocking reaction : 150 mL

Weight of m-methoxyphenol : 8.19 grams (0.066 moles)

DBTDL as catalyst : 5 drops

Temperature of blocking reaction : 50°C

Time for completing the blocking reaction : 4-5 days

More THF solvent used for dilution : 100 mL

Total vol.of petroleum ether used for Precipitation :3500 mL

Weight of the product : 13.2 grams (68% yield)

B. Pentaerythritol-TDI-HEMA-Blocking Agent Synthesis:

1. Preparation of Pentaerythritol-TDI Adduct: In this case, the adducting reaction was carried out in a heterogeneous system. The same apparatus previous section were used.

34.0 grams (0.250 moles) of pentaerythritol was ground into a fine powder, and then dried in a vacuum oven at 40°C for one day. The dried powder was placed in a flask and 500 mL of distilled p-dioxane, 261 grams (1.5 moles, 50% excess) of TDI, and 5 drops of DBTDL were added to it. The reaction was now carried out under nitrogen circulation and vigorous agitation. It was found that pentaerythritol was insoluble in p-dioxane.

Since p-dioxane is a very good solvent for pentaerythritol-TDI adduct, once the adduct was formed, it dissolved in the p-dioxane immediately. In this way the adduct product was easily separated from the pentaerythritol. Similarly, The reaction of hydroxy group of pentaerythritol with isocyanate group of TDI occurred exothermically. In order to avoid the formation of gel material due to by-product reactions, a cooling water bath had to be used.

As the reaction proceeded, the total amount of pentaerythritol was observed to gradually diminish. At the same time the colorless solution turned yellow and became more viscous. Generally, the fresh distilled p-dioxane had to be poured into the flask to prevent oversaturation at this time. In the case of oversaturation another 50 mL of distilled p-dioxane had to be added to the reacting solution every 2-3

hours. The reaction was continued until the amount of pentaerythritol was observed to remain constant.

2. Precipitation of Pentaerythritol-TDI Adduct: Upon completion of the reaction, the solution of pentaerythritol-TDI was filtered to remove the unreacted solid pentaerythritol in petroleum ether. The precipitating procedures described in part 4 of section A can be applied to this case. Finally, the milky solid material obtained was dried and found to weigh 128.5 grams (yield of 61.9%).

3. Blocking the Pentaerythritol-TDI Adduct: In the blocking reaction, the 1:1 molar ratio of HEMA (2-hydroxy ethyl methacrylate) and each of the four blocking agents were used to block the samples of pentaerythritol-TDI adduct. Although four different blocking agents were applied in the blocking reaction, only the blocking reaction of p-cresol will be described in detail in this section. For the remaining three blocking agents, the reaction conditions, such as temperature, required time for completion of the blocking reaction, and excess amount of blocking agents etc., are individually listed in Table II-IV.

8.0 grams of pentaerythritol-TDI adduct from part 2 of section B were placed in a 250 mL Erlenmeyer flask and 100 mL of dry THF were added to it dissolve the pentaerythritol-TDI adduct. Upon the addition of THF, the solution turned a reddish brown color. p-cresol, 2.2863 grams (0.021 moles or 20% excess), 2.576 grams (0.0198 moles or 60% excess) of HEMA, and 6 drops of DBTDL as catalyst were simultaneously

poured into the solution which was gently shaken to ensure that all reactants were thoroughly mixed. Nitrogen gas was passed through it for about 1 to 2 minutes. The flask was capped with a rubber stopper, which was wrapped in aluminum foil. The blocking reaction proceeded in a oil bath, maintained at 50°C. Using the same procedure as described in the previous section, an Infrared Spectrometer was used to check for the free isocyanate peak. In the case of p-cresol blocking reaction, it was found that the free isocyanate peak had reached its minimum after seven days. In order to ensure completion of the blocking reaction, as indicated by the absence of free isocyanate peak, 0.4172 grams of p-cresol was added to the blocking solution. One day later, the free isocyanate peak was completely eliminated. The blocking solution was now diluted with 90 mL of dry THF to obtain a good precipitation.

4. The Precipitation of Pentaerythritol-TDI-HEMA-p-cresol. The solution from above was precipitated in petroleum ether. All precipitating procedures are similar to those described in part 4 of section A. Finally, 10.2 grams (84% yield) of pentaerythritol-TDI-HEMA-p-cresol was obtained.

Table II Preparation of Pentaerythritol-TDI-HEMA-Eugenol

The general procedure is the same that was described in parts 3,4 of section B with following quantities of the reactant and characteristics:

Weight of pentaerythritol-TDI adduct: 8.0 grams
(9.61×10^{-3} moles)

THF solvent used in blocking reaction : 100 mL

Weight of HEMA : 2.576 grams (0.0198 moles)

Weight of Eugenol 3.47 grams (0.021 moles, 18% excess)

DBTDL as catalyst : 5 drops

Temperature of the blocking reaction : 45°C

More Eugenol added for completing the blocking
reaction after 7 days : 0.63 grams (3.8×10^{-4} moles, 4% excess)

Time for completing blocking reaction : 13 days

More THF solvent used for dilution : 150 mL

Total volume of petroleum ether used

for precipitation : 3500 mL

Weight of product : 9.8 grams (72% yield)

Table III Preparation of Pentaerythritol-TDI-HEMA-o-Methoxy-phenol

The general procedure is the same that was described in parts 3,4 of section B with following quantities of the reactant and characteristics:

Weight of pentaerythritol-TDI Adduct: 8 grams

(9.61×10^{-3} moles)

THF solvent used in the blocking reaction : 100 mL

Weight of HEMA : 2.576 grams (0.0198 moles)

Weight of o-methoxyphenol: 2.62 grams

(0.021 moles, 18% excess)

DBTDL as catalyst : 5 drops

Temperature of blocking reaction : 45°C

More o-methoxyphenol added for completing blocking reaction after 7 days : 0.48 grams (3.8×10^{-4} moles, 4% excess)

Time for completing the locking reaction : 11 days

More THF solvent used for dilution after 7-8 days : 150 mL

Total volume of petroleum ether used for precipitation : 3500 mL

Weight of product : 8.7 grams (67.5% yield)

Table IV Preparation of Pentaerythritol-TDI-HEMA-o-Chloro-phenol

The general procedure is the same that was described in parts 3,4 of section B with following quantities of the reactant and characteristics:

Weight of pentaerythritol-TDI adduct : 10 grams(0.012 moles)

THF solvent used in blocking reaction : 100 mL

Weight of HEMA : 3.23 grams(0.02484 moles, 7% excess)

Weight of o-chlorophenol : 3.47 grams

(0.027 moles, 25% excess)

DBTDL as catalyst : 5 drops

Temperature of blocking reaction : 37°C

More o-chlorophenol added for completing the blocking reaction after two weeks : 2.00 grams

(1.11×10^{-3} moles, 9% excess)

Time for completing the blocking reaction : 19 days

More solvent used for dilution : 200 mL

Total volume of petroleum ether used for

Precipitation : 3500 mL

Weight of product : 11.4 grams (70.4% yield)

C. Hydroxyhexyl Monomethacrylates

1. Preparation of Hydroxyhexyl Monomethacrylates: the reaction of hydroxyl group of 1,6-hexanediol with the carboxyl group of methacrylic acid proceeded at 80°C and 100-150 mm Hg under an oxygen atmosphere. The apparatus was set up as indicated in Appendix B. The detailed experimental procedures are as follows:

137.7 grams (1.6 moles) of methacrylic acid, 189.1 grams (1.6 moles) of 1,6-hexanediol, 1.5 grams of p-Toluene sulfonic acid monohydrate (as catalyst), and 0.6 grams of di-tert-butyl -p-cresol (antioxidant) were poured into a 500 mL resin kettle and gently shaken to ensure proper mixing. The reactants were heated to 80°C and oxygen gas was carefully introduced. At the same time, a vacuum of 100-150 mmHg was developed by using a vacuum pump and controlled by using the regulator. As long as a temperature of 80°C and a pressure of 100-150 mmHg was maintained, water was observed to condense in the collecting flask and the trap. For this reaction, temperature and oxygen gas are the most important factors. In fact, the best reaction rate can be obtained at 80°C . Beyond this temperature, the polymerization reaction would occur at the double bond of methacrylic acid. The purpose of introducing oxygen gas was to inhibit the polymerization reaction, thereby obtaining a higher yield of the product. The reaction was continued until all the water, a by product, was removed. The final product was 190 mL.

2. Purification of 6-Hydroxyhexyl monomethacrylates: The

liquid from above part contained both monoester and diester. The monoester was separated from diester by extracting the diester with n-octane three times. Using 600 mL of n-octane each time. Finally, 55.0 grams (16.8% yield) of yellow liquid was obtained.

II. Characterization

1. Melting Points of Monomers: In determining the melting points of the monomers, a light microscope with a hot stage and a crossed-polarized lens made by Bristoline Company was used. For each of the monomers, the melting point determinations were performed twice. A heating rate of approximately $1^{\circ}\text{C} / 1 \text{ min}$ was used to obtain a precise melting point. The melting points for all of monomers are listed in Table V
2. IR Spectra :The samples except for the hydroxyhexyl monomethacrylates were KBr pellets. The monomer, 1.4×10^{-3} grams, was mixed with 0.5 grams of KBr, and ground together using an agate mortar and pestle. The sample discs were made with a Carver press, and the IR instrument was the Perkin--Elemer Infrared Spectrophotometer model 1310. IR data are given in Tables VI-XIV. IR Spectra are shown in Figs 1-9.
3. NMR Spectra: Only proton NMR was used. Unisol or acetone was used as solvent, and TMS as reference. The samples were dissolved in the solvent and filtered through 0.45 micro nitro-cellulose filters. The instrument used was the Perkin- Elemer EM 360L. The NMR data are given in Tables XV-XXII. NMR Spectra for all of monomers are shown in Figs 10-17.
4. Elemental Analysis: This analyses were performed by Mic Anal Corporation of Tuscon, Arizona. The reported percentage of Carbon, Hydrogen, Nitrogen, and Chlorine are given in Tables XXIII-XXX.
5. Tensile Strength Test: The procedure for preparing the samples for tensile strength testing is as follows:

- a. Preparation of Aluminum rods: The faces of the rods, which were sandblasted for better adhesion, were put into petroleum ether in an ultra sound machine for 5 minutes for degreasing. The $\text{Na}_2\text{Cr}_2\text{O}_7/\text{H}_2\text{SO}_4$ etching solution was used to etch the faces of the rods, which were then rinsed with tap water and followed by distilled water. Finally, the rods were set face up in a Jig with rubber sleeves around them to minimize the leakage of the adhesive.
- b. Tooth Slices Treatment: Tooth slices were immersed in 5% citric acid for 2 minutes and then washed with distilled water for 1 minute. The etched tooth slices were soaked with DME (1,2-Dimethoxy ethane) for two minutes. The monomers made in section A and B were dissolved in DME to form an adhesive solution. The tooth slices which were previously soaked in DME were now placed in the adhesive solution.
- c. Sample Making: PMMA-MMA mixture (75% MMA, 25% PMMA) along with NNDMPT as catalyst and benzoyl peroxide as initiator was placed on the treated rods in the Jig. The treated tooth slices were now dipped in PMMA-MMA mixture and immediately placed on the faces of the rods. Finally, Six samples were subjected to a load of 1875 grams for about one hour. The bonded tooth slices were then measured for their tensile breaking strength in a SCOTT-CRE 1500 Tensile Testing Machine. The results of the testing for each of monomers are listed in Tables XXXI-XXXX.

Table V Melting Point of The Products

| Compound | Melting Point |
|---|---------------|
| HPMA-TDI Adduct | 185-187°C |
| HPMA-TDI-P-Cresol | 85-87°C |
| HPMA-TDI-m-Methoxy Phenol | 83-86°C |
| Pentaerythritol-TDI | 305-307°C |
| Pentaerythritol-TDI-HEMA-P-Cresol | 104-108°C |
| Pentaerythritol-TDI-HEMA-Eugenol | 103-105°C |
| Pentaerythritol-TDI-HEMA-o-Methoxy Phenol | 122-125°C |
| Pentaerythritol-TDI-HEMA-o-Cholorophenol | 119-122°C |

Table VI Selected IR Absorptions of HPMA - TDI

| Assignments | Wave number cm^{-1} |
|------------------------------------|------------------------------|
| N-H stretch | 3350 (s) |
| C-H aliphatic and aromatic stretch | 2960 (s) |
| N=C=O | 2280 (s) |
| C=O carbonyl | 1740 (s) |
| C=C | 1640 (m) |
| C-H aromatic skeletal stretch | 1530 (s) |
| CH ₂ bending | 1460 (s) |
| CH ₃ bending | 1390 (s) |
| C-O | 1300 (s) |
| C-N stretch | 1230 (s) |
| C-N stretch | 1170 (s) |
| C-O | 1120 (m) |
| C-O | 1090 (s) |
| C-O | 1050 (m) |
| C-H out of plane deformation | 1000 (m) |
| C-H out of plane deformation | 950 (m) |
| C-H out of plane deformation | 870 (m) |
| C-H out of plane deformation | 820 (m) |
| C-H out of plane deformation | 760 (m) |

Table VII Selected IR Absorptions of HPMA-TDI-P-Cresol

| Assignments | Wave number cm^{-1} |
|--------------------------------|------------------------------|
| N-H stretch | 3320 (s) |
| C-H aliphatic stretch aromatic | 2880 & 2990 (s) |
| C=O carbonyl | 1720 (s) |
| C=C | 1600 (m) |
| C-H aromatic skeletal stretch | 1530 (s) |
| C-H aromatic skeletal stretch | 1510 (s) |
| CH ₂ bending | 1450 (s) |
| CH ₃ bending | 1360 (m) |
| CH ₃ bending | 1330 (m) |
| C-N stretch | 1270 (m) |
| C-O | 1230 (s) |
| C-O | 1210 (s) |
| C-N stretch | 1190 (s) |
| C-H in plane bend | 1070 (s) |
| C-H out of plane deformation | 910 (s) |
| C-H out of plane deformation | 820 (m) |

Table VIII Selected IR Absorptions of HPMA-TDI-m-Methoxy-
phenol

| Assignments | Wave number cm^{-1} |
|------------------------------------|------------------------------|
| N-H stretch | 3290 (s) |
| C-H aliphatic and aromatic stretch | 2880 & 2900 (s) |
| C=O carbonyl | 1720 (s) |
| C=C | 1600 (s) |
| C-H aromatic skeletal stretch | 1530 (s) |
| C-H aromatic skeletal stretch | 1490 (s) |
| CH ₂ bending | 1460 (s) |
| CH ₃ bending | 1360 (m) |
| C-O | 1290 (s) |
| C-N stretch | 1230 (s) |
| C-N stretch | 1190 (s) |
| C-O | 1170 (s) |
| C-O | 1150 (s) |
| C-H in plane | 1070 (s) |
| C-H out of plane deformation | 950 (m) |
| C-H out of plane deformation | 910 (s) |
| C-H out of plane deformation | 850 (m) |
| C-H out of plane deformation | 770 (m) |
| C-H out of plane deformation | 690 (m) |

Table IX Selected IR Absorptions of Pentarythritol-TDI

| Assignment | Wave Number cm^{-1} |
|------------------------------------|------------------------------|
| N-H stretch | 3320 (s) |
| C-H aliphatic and aromatic stretch | 2920 & 2960 (m) |
| N=C=O | 2270 (s) |
| C=O | 1720 (s) |
| C-H aromatic skeletal stretch | 1600 (s) |
| C-H aromatic skeletal stretch | 1520 (s) |
| CH ₂ bend | 1390 (m) |
| C-O | 1270 (m) |
| C-N stretch | 1220 (s) |
| C-N stretch | 1160 (s) |
| C-H in plane | 1000 (m) |
| C-H out of plane deformation | 930 (m) |
| C-H out of plane deformation | 860 (m) |
| C-H out of plane deformation | 810 (m) |
| C-H out of plane deformation | 760 (m) |

Table X Selected IR Absorptions of Pentaerythritol-TDI-
HEMA-P-Cresol

| Assignment | Wave Number cm^{-1} |
|------------------------------------|------------------------------|
| N-H | 3320 (s) |
| C-H aliphatic and aromatic stretch | 2920, 2980 (m) |
| C=O | 1720 (s) |
| C=C | 1600 (s) |
| C-H aromatic skeletal stretch | 1530 (m) |
| C-H aromatic skeletal stretch | 1450 (m) |
| CH ₂ bend | 1410 (s) |
| CH ₃ bend | 1300 (s) |
| C-N | 1230 (s) |
| C-O | 1200 (s) |
| C-O | 1070 (s) |
| C-H in plane bend | 1000 (m) |
| C-H out of plane deformation | 950 (m) |
| C-H out of plane deformation | 870 (m) |
| C-H out of plane deformation | 820 (m) |
| C-H out of plane deformation | 760 (m) |

Table XI Selected IR Absorptions of Pentaerythritol-TDI-
HEMA-Eugenol

| Assignment | Wave Number cm^{-1} |
|------------------------------------|------------------------------|
| N-H | 3330 (s) |
| C-H aliphatic and aromatic stretch | 2900 (m) |
| C=O | 1730 (s) |
| C=C | 1610 (s) |
| C-H aromatic skeletal stretch | 1540 (s) |
| C-H aromatic skeletal stretch | 1460 (m) |
| CH ₂ bend | 1430 (m) |
| CH ₃ bend | 1330 (m) |
| C-N | 1240 (s) |
| C-N | 1210 (s) |
| C-O | 1200 (s) |
| C-O | 1150 (s) |
| C-O | 1080 (s) |
| C-H in plane bend | 1010 (m) |
| C-H out of plane deformation | 960 (m) |
| C-H out of plane deformation | 880 (m) |
| C-H out of plane deformation | 830 (m) |
| C-H out of plane deformation | 770 (m) |

Table XII Selected IR Absorptions of Pentarsethritol-TDI-
HEMA-o-Methoxyphenol

| Assignment | Wave Number cm^{-1} |
|------------------------------------|------------------------------|
| N-H stretch | 3380 (s) |
| C-H aliphatic and aromatic stretch | 2920 & 2960 (m) |
| C=O | 1710 (s) |
| C=C | 1600 (s) |
| C-H aromatic skeletal stretch | 1530 (s) |
| C-H aromatic skeletal stretch | 1440 (m) |
| CH ₂ bend | 1410 (m) |
| CH ₃ bend | 1310 (m) |
| C-N stretch | 1290 (m) |
| C-O | 1220 (m) |
| C-N stretch | 1170 (s) |
| C-O | 1130 (m) |
| C-O | 1060 (s) |
| C-H in plane | 1000 (m) |
| C-H out of plane deformation | 940 (m) |
| C-H out of plane deformation | 870 (m) |
| C-H out of plane deformation | 810 (m) |
| C-H out of plane deformation | 760 (m) |


Table XIII Selected IR Absorptions of Pentaerythritol-TDI-
HEMA-o-Chlorophenol

| Assignment | Wave Number cm |
|------------------------------------|-----------------|
| N-H stretch | 3400 (s) |
| C-H aliphatic and aromatic stretch | 2920 & 2940 (m) |
| C=O | 1700 (s) |
| C=C | 1600 (s) |
| C-H aromatic skeletal stretch | 1530 (s) |
| C-H aromatic skeletal stretch | 1440 (s) |
| CH ₂ bend | 1410 (m) |
| CH ₃ bend | 1310 (m) |
| C-N stretch | 1290 (m) |
| C-O | 1220 (s) |
| C-N | 1170 (s) |
| C-O | 1130 (m) |
| C-O | 1060 (s) |
| C-H in plane bend | 1000 (m) |
| C-H out of plane deformation | 950 (m) |
| C-H out of plane deformation | 870 (m) |
| C-H out of plane deformation | 810 (m) |
| C-H out of plane deformation | 760 (m) |

Table XIV Selected IR Absorptions of Hydroxyhexyl-
methacrylate


| Assignment | Wave Number cm^{-1} |
|------------------------------|------------------------------|
| O-H stretch | 3330 |
| C-H Aliphatic stretch | 2880 & 2920 |
| C=O | 1710 |
| C=C | 1640 |
| CH (alkane) bend | 1450 |
| CH (alkane) bend | 1430 |
| CH (alkene) bend | 1410 |
| O-H bend | 1300 |
| C-O stretch | 1170 |
| C-O-C | 1020 & 1060 |
| OH bend | 950 |
| C-H out of plane deformation | 820 |

Table XVI NMR Signals of HPMA-TDI-p-Cresol

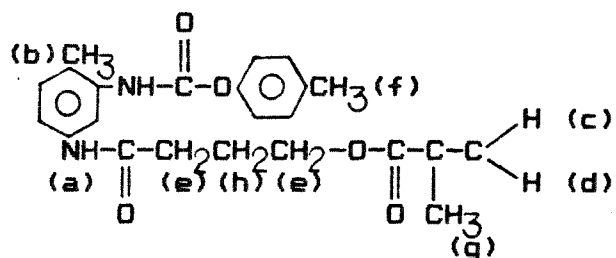


| | |
|----|--------------------|
| a. | ? |
| b. | 7.0-8.0 δ (?) (6H) |
| c. | 6.10 δ (s) (1H) |
| d. | 5.60 δ (s) (1H) |
| e. | 4.30 δ (d) (3H) |
| f. | 2.20 δ (d) (?) |
| g. | 1.90 δ (s) (4H) |
| h. | 1.30 δ (d) (5H) |

Table XVIII NMR Signals of Pentaerythritol-TDI

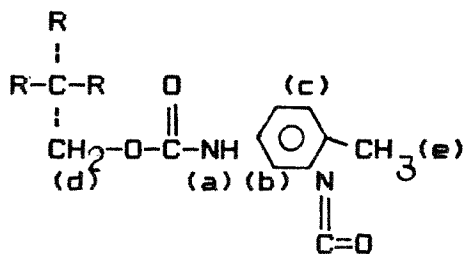

| | |
|----|-------------------------|
| a. | 9.25 δ (s) (4H) |
| b. | 7.30 δ (s) (4H) |
| c. | 7.10 δ (d) (9H) |
| d. | 4.30 δ (s) (7H) |
| e. | 2.20 δ (s) (13H) |

Table XIX NMR Signals of Pentaerythritol-TDI-HEMA-
p-Cresol

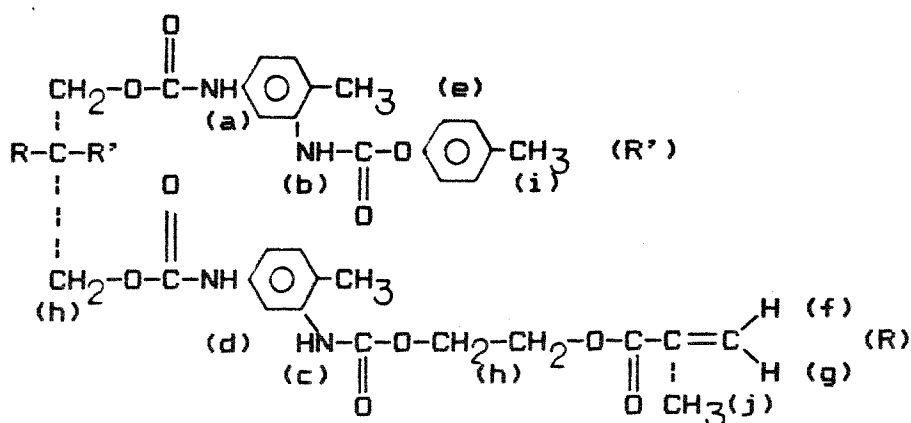

| | | | |
|----|---------------|-----|--------|
| a. | 9.25 δ | (s) | (4H) |
| b. | 8.65 δ | (s) | (1.3H) |
| c. | 8.10 δ | (s) | (2.7H) |
| d. | 7.75 δ | (s) | (4H) |
| e. | 7.10 δ | (t) | (14H) |
| f. | 6.10 δ | (s) | (2H) |
| g. | 5.60 δ | (s) | (2H) |
| h. | 4.35 δ | (s) | (18H) |
| i. | 2.30 δ | (d) | (18H) |
| j. | 1.90 δ | (s) | (8H) |

Table XX NMR Signals of Pentaerythritol-TDI-HEMA-Eugenol



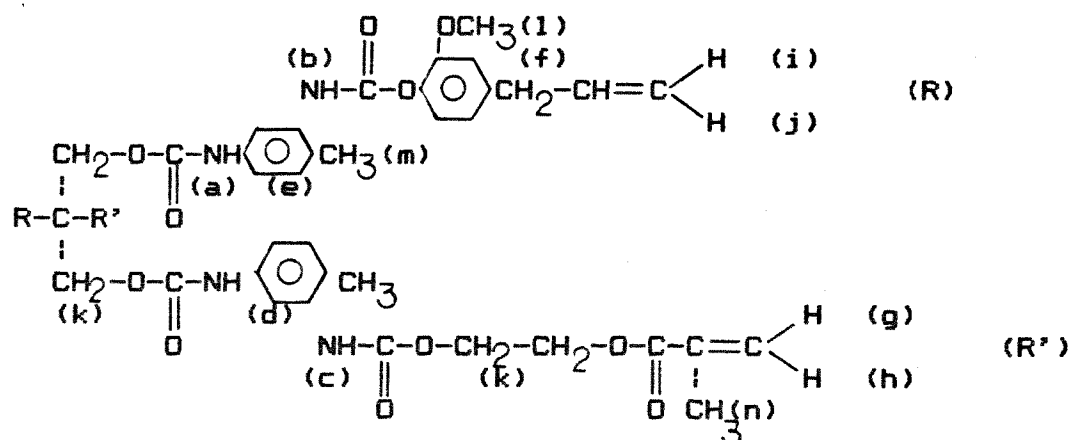


Table XXI NMR Signals of Pentaerythritol-TDI-HEMA-
o-Methoxyphenol

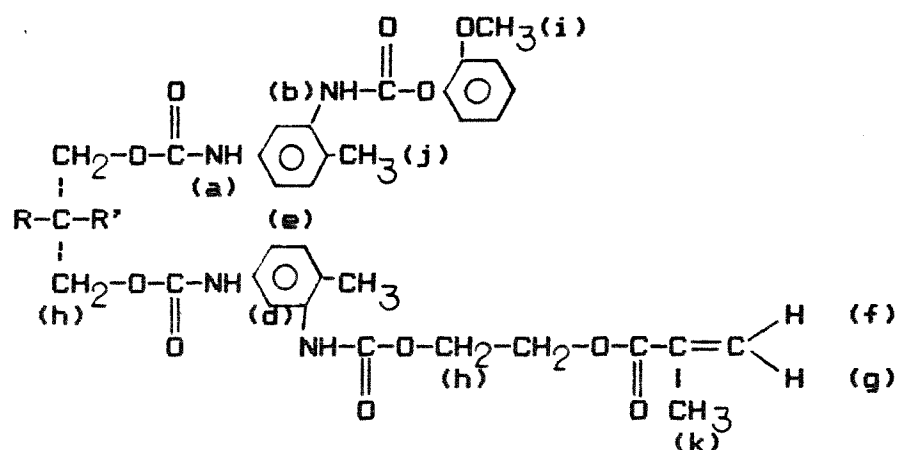

| | |
|----|------------------|
| a. | 9.30 δ (s) (4H) |
| b. | 8.80 δ (s) (1H) |
| c. | 8.20 δ (s) (3H) |
| d. | 7.60 δ (s) (5H) |
| e. | 7.00 δ (d) (18H) |
| f. | 6.10 δ (s) (3H) |
| g. | 5.60 δ (s) (3H) |
| h. | 4.30 δ (s) (24H) |
| i. | 3.80 δ (s) (5H) |
| j. | 2.20 δ (s) (20H) |
| k. | 1.90 δ (s) (15H) |

Table XXII NMR Signals of Pentaerythritol-TDI-HEMA-
o-Chlorophenol

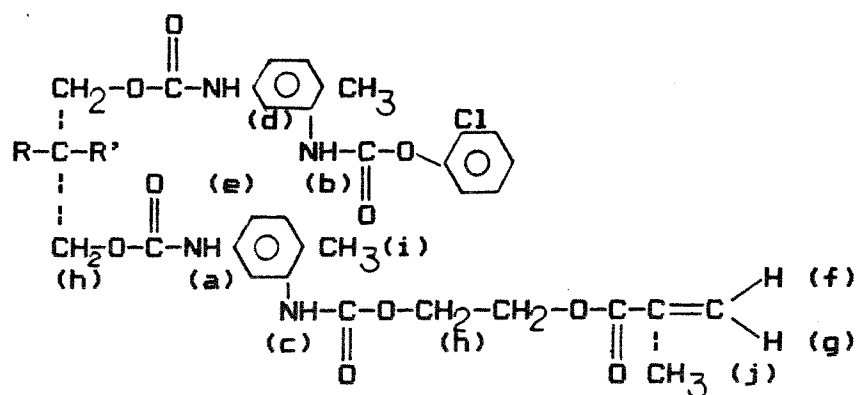

| | | | |
|----|---------------|-----|-------|
| a. | 9.30 δ | (s) | (4H) |
| b. | 9.10 δ | (s) | (1H) |
| c. | 8.30 δ | (s) | (3H) |
| d. | 7.70 δ | (s) | (5H) |
| e. | 7.10 δ | (d) | (25H) |
| f. | 6.10 δ | (s) | (3H) |
| g. | 5.60 δ | (s) | (3H) |
| h. | 4.35 δ | (s) | (24H) |
| i. | 2.20 δ | (s) | (20H) |
| j. | 1.90 δ | (s) | (12H) |

Table XXIII Elemental Analysis of Hydroxyhexylmethacrylate :

| | Observed (%) | Theoretical (%) |
|---|--------------|-----------------|
| C | 63.45 | 64.5 |
| H | 10.09 | 9.67 |

Table XXIV Elemental Analysis of HPMA-TDI-p-Cresol :

| | Observed (%) | Theoretical (%) |
|---|--------------|-----------------|
| C | 64.76 | 64.77 |
| H | 6.03 | 6.15 |
| N | 9.21 | 6.57 |

Table XXV Elemental Analysis of HPMA-TDI-m-Methoxyphenol :

| | Observed (%) | Theoretical (%) |
|---|--------------|-----------------|
| C | 62.11 | 62.43 |
| H | 5.97 | 5.92 |
| N | 8.00 | 6.33 |

Table XXVI Elemental Analysis of Pentaerythritol-TDI :

| | Observed (%) | Theoretical (%) |
|---|--------------|-----------------|
| C | 59.06 | 59.13 |
| H | 4.52 | 4.36 |
| N | 13.73 | 13.46 |

**Table XXVII Elemental Analysis of Pentaerythritol-TDI-HEMA-
p-Cresol (In four free isocyanate position, 30%
being substituted by p-cresol, 70% by HEMA) :**

| | Observed (%) | Theoretical (%) |
|---|--------------|-----------------|
| C | 59.92 | 59.20 |
| H | 5.60 | 5.40 |
| N | 8.44 | 9.22 |

**Table XXVIII Elemental Analysis of Pentaerythritol-TDI-HEMA-
Eugenol (In four free isocyanates, 30% being
substituted by Eugenol, 70% by HEMA)**

| | Observed (%) | Theoretical (%) |
|---|--------------|-----------------|
| C | 60.04 | 60.10 |
| H | 5.56 | 5.67 |
| N | 8.59 | 8.04 |

**Table XXIX Elemental Analysis of Pentaerythritol-TDI-HEMA-
o-Methoxyphenol (In four free isocyanates, 25%
being substituted by o-methoxyphenol, 75% by HEMA)**

| | Observed (%) | Theoretical (%) |
|---|--------------|-----------------|
| C | 58.02 | 58.83 |
| H | 5.36 | 5.54 |
| N | 9.90 | 8.32 |

Table XXX Elemental Analysis of Pentaerythritol-TDI-HEMA-
o-Chlorophenol (In four free isocyanates, 20% being
substituted by o-Chlorophenol, 80% by HEMA)

| | Observed (%) | Theoretical (%) |
|----|--------------|-----------------|
| C | 57.77 | 57.74 |
| H | 5.04 | 5.38 |
| N | 9.70 | 8.29 |
| Cl | 1.36 | 2.09 |

Table XXXI Bonding Strength of Pentaerythritol-TDI-HEMA-

P-cresol

Filling Material: 75% MMA- 25% PMMA

Setting Time : 48 hours

Period of Storage in Water : 0

Promoter: New NNDMPT

| Sample Number | Bonding Strength (psi) |
|----------------------------------|------------------------|
| 1 | 1273 |
| 2 | 1160 |
| 3 | 953 |
| 4 | 2277 |
| 5 | 1382 |
| 6 | 1193 |
| 7 | 1783 |
| 8 | 1630 |
| 9 | 2139 |
| 10 | 1288 |
| Average Bonding Strength (psi) = | 1508 |

Table XXXII Bonding Strength of Pentaerythritol-TDI-HEMA-**P-cresol****Filling Material: 75% MMA- 25% PMMA****Setting Time : 48 hours****Period of Storage in Water : 168 hours****Promoter: New NNDMPT**

| Sample Number | Bonding Strength (psi) |
|---|-------------------------------|
| 1 | 327 |
| 2 | 233 |
| 3 | 284 |
| 4 | 502 |
| 5 | 364 |
| Average Bonding Strength (psi) = | 342 |

Table XXXIII Bonding Strength of Pentaerythritol-TDI-HEMA-**P-cresol****Filling Material: 75% MMA- 25% PMMA****Setting Time : 48 hours****Period of Storage in Water : 240 hours****Promoter: New NNDMPT**

| Sample Number | Bonding Strength |
|---|-------------------------|
| 1 | 335 |
| 2 | 167 |
| 3 | 175 |
| 4 | 218 |
| Average Bonding Strength (psi) = | 224 |

Table XXXIV Bonding Strength of Pentaerythritol-TDI-HEMA-

P-cresol

Filling Material: 75% MMA-25% PMMA

Setting Time : 96 hours

Period of Storage in Water : 168 hours

Promoter: Old NNDMPT

| Sample Number | Bonding Strength |
|----------------------------------|------------------|
| 1 | 357 |
| 2 | 371 |
| 3 | 335 |
| 4 | 895 |
| 5 | 327 |
| 6 | 400 |
| Average Bonding Strength (psi) = | 448 |

Table XXXV Bonding Strength of Pentaerythritol-TDI-HEMA-

P-cresol

Filling Material: 75% MMA-25% PMMA

Setting Time : 0

Period of Storage in Water : 48 hours

Promoter: Old NNDMPT

| Sample Number | Bonding Strength |
|----------------------------------|------------------|
| 1 | 1783 |
| 2 | 1273 |
| 3 | 1288 |
| 4 | 1281 |
| 5 | 2270 |
| 6 | 1302 |
| 7 | 1426 |
| Average Bonding Strength (psi) = | 1518 |

Table XXXVI Bonding Strength of Pentaerythritol-TDI-HEMA-

P-cresol

Filling Material: 75% MMA-25% PMMA

Setting Time : 48 hours

Period of Storage in Water : 336 hours

Promoter: Old NNDMPT

| Sample Number | Bonding Strength |
|----------------------------------|------------------|
| 1 | 982 |
| 2 | 1921 |
| 3 | 895 |
| Average Bonding Strength (psi) = | 1266 |

Table XXXVII Bonding Strength of Pentaerythritol-TDI-HEMA-o-MethoxyPhenol

Filling Material: 75% MMA- 25% PMMA

Setting Time : 0

Period of Storage in Water : 960 hours

Promoter: Old NNDMPT

| Sample Number | Bonding Strength (psi) |
|----------------------------------|------------------------|
| 1 | 815 |
| 2 | 880 |
| 3 | 407 |
| 4 | 233 |
| Average Bonding Strength (psi) = | 584 |

Table XXXVIII Bonding Strength of Pentaerythritol-TDI-HEMA-
o-Methoxyphenol

Filling Material: 75% MMA-25% PMMA

Setting Time : 0

Period of Storage in Water : 984 Hours

Promoter: Old NNDMPT

| Sample Number | Bonding Strength (psi) |
|----------------------------------|------------------------|
| 1 | 102 |
| 2 | 160 |
| 3 | 306 |
| 4 | 153 |
| 5 | 182 |
| Average Bonding Strength (psi) = | 181 |

Table XXXIX Bonding Strength of Pentaerythritol-TDI-HEMA-o-Chlorophenol

Filling Material: 75% MMA-25% PMMA

Setting Time : 0

Period of Storage in Water : 24 hours

Promoter: Old NNDMPT

| Sample Number | Bonding Strength (psi) |
|----------------------------------|------------------------|
| 1 | 1499 |
| 2 | 2619 |
| 3 | 2466 |
| 4 | 2648 |
| 5 | 2474 |
| average Bonding Strength (psi) = | 2341 |

Table XXXX Bonding Strength of Pentaerythritol-TDI-HEMA-o-
Chlorophenol

Filling Material: 75% MMA-25% PMMA

Setting Time : 0

Period of Storage in Water : 48 hours

SPromoter: Old NNDMPT

| Sample Number | Bonding Strength (psi) |
|----------------------------------|------------------------|
| 1 | 2081 |
| 2 | 888 |
| 3 | 1593 |
| Average Bonding Strength (psi) = | 1521 |

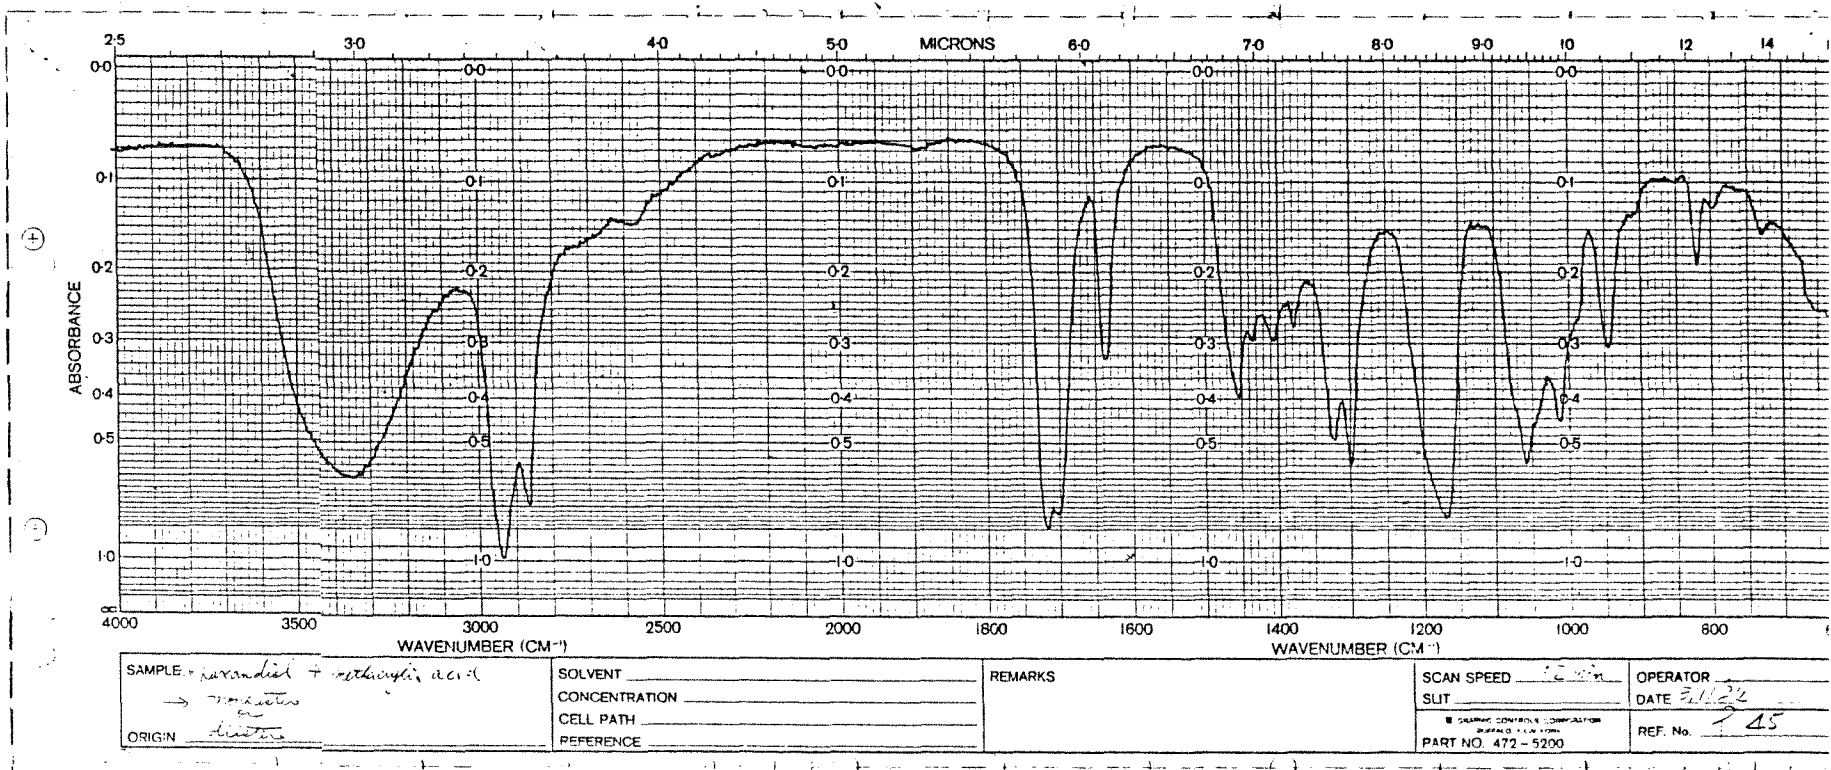


Fig.1 IR Spectra of Hydroxyhexylmethacrylate

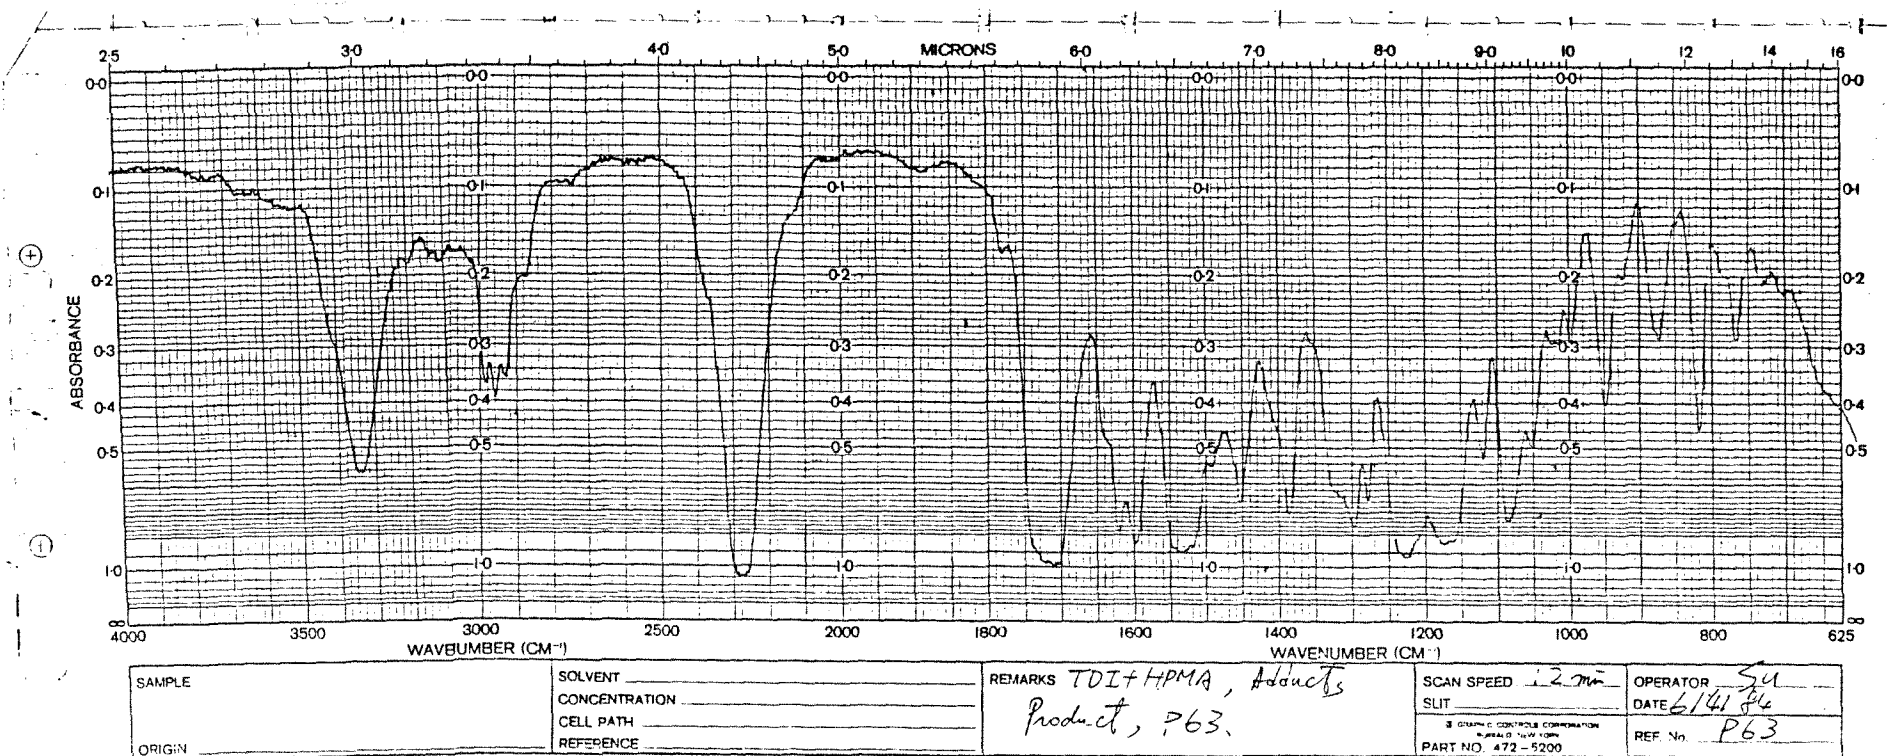


Fig. 2 IR Spectra of HPMA-TDI

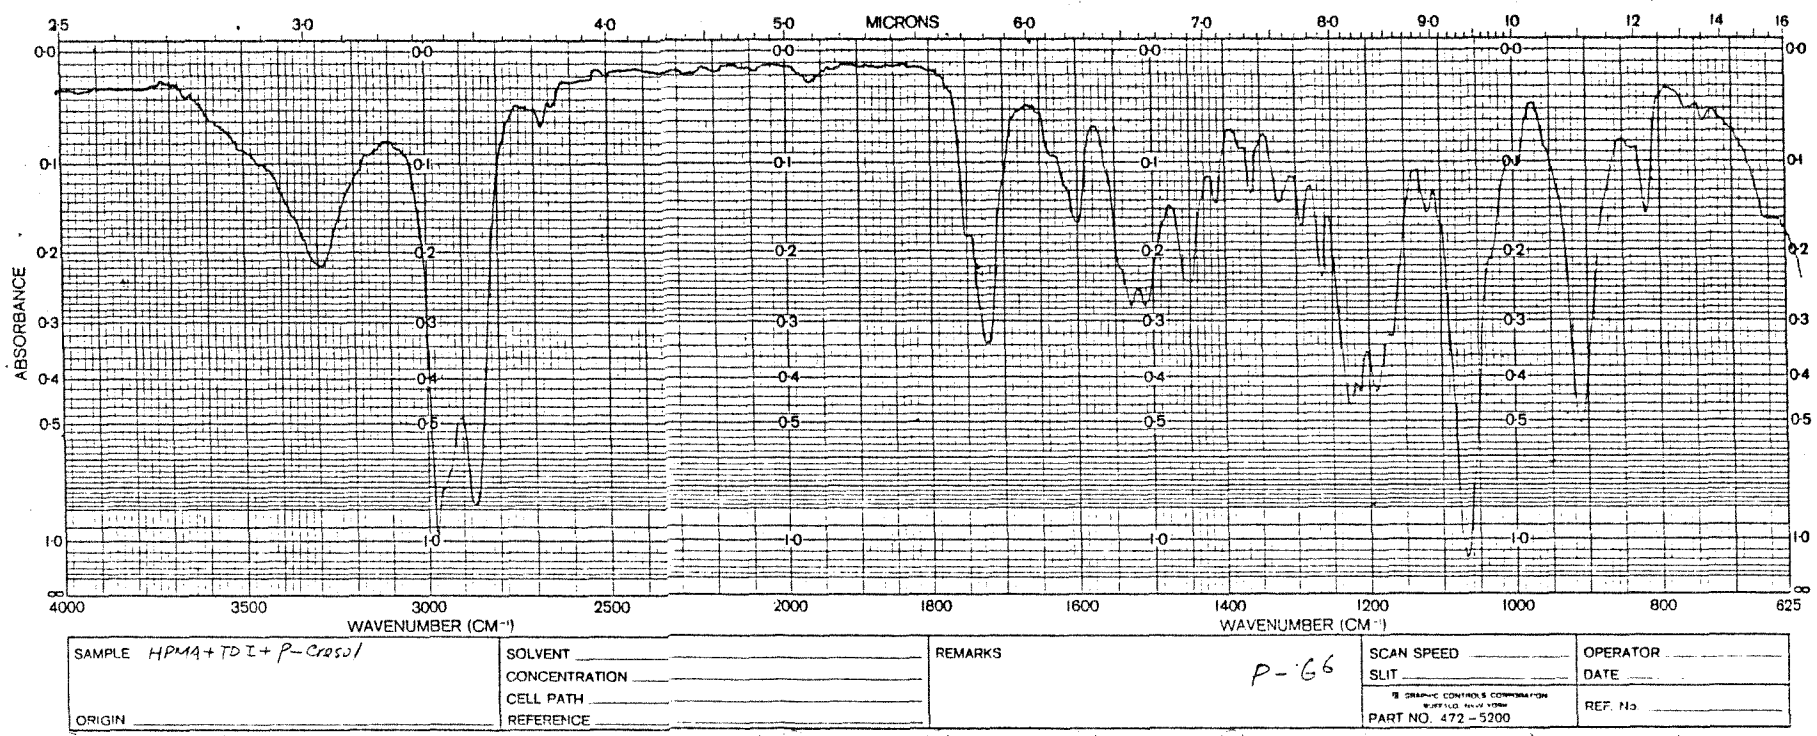


Fig. 3 IR Spectra of HPMA-TDI-p-Cresol

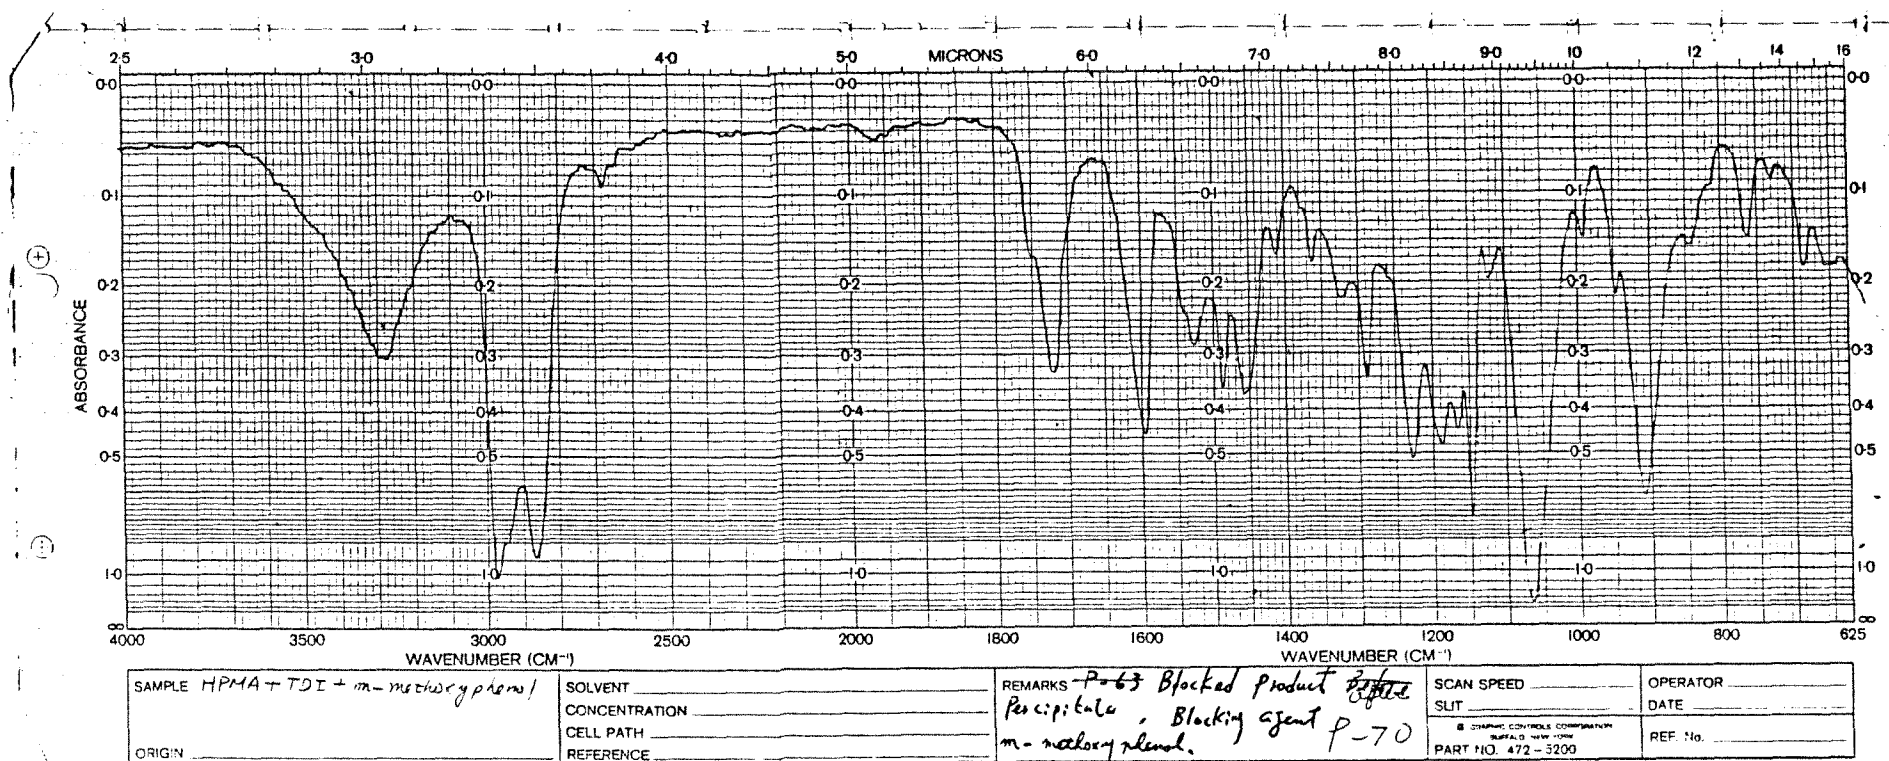


Fig. 4 IR Spectra of HPMA-TDI-m-Methoxyphenol

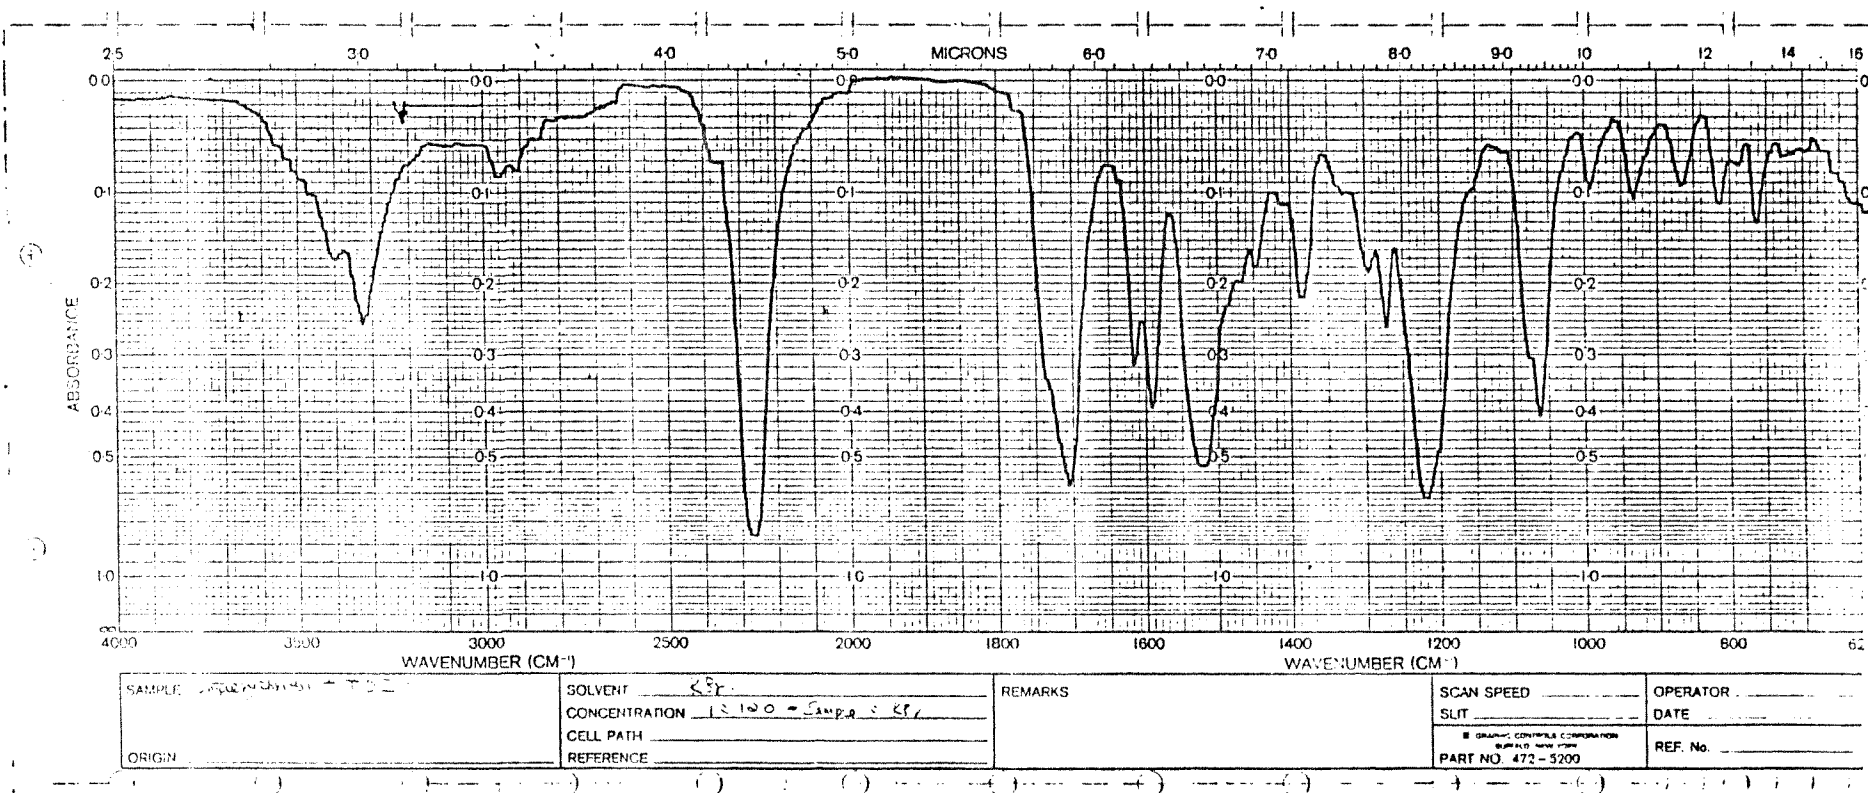


Fig. 5 IR Spectra of Pentaerythritol-TDI

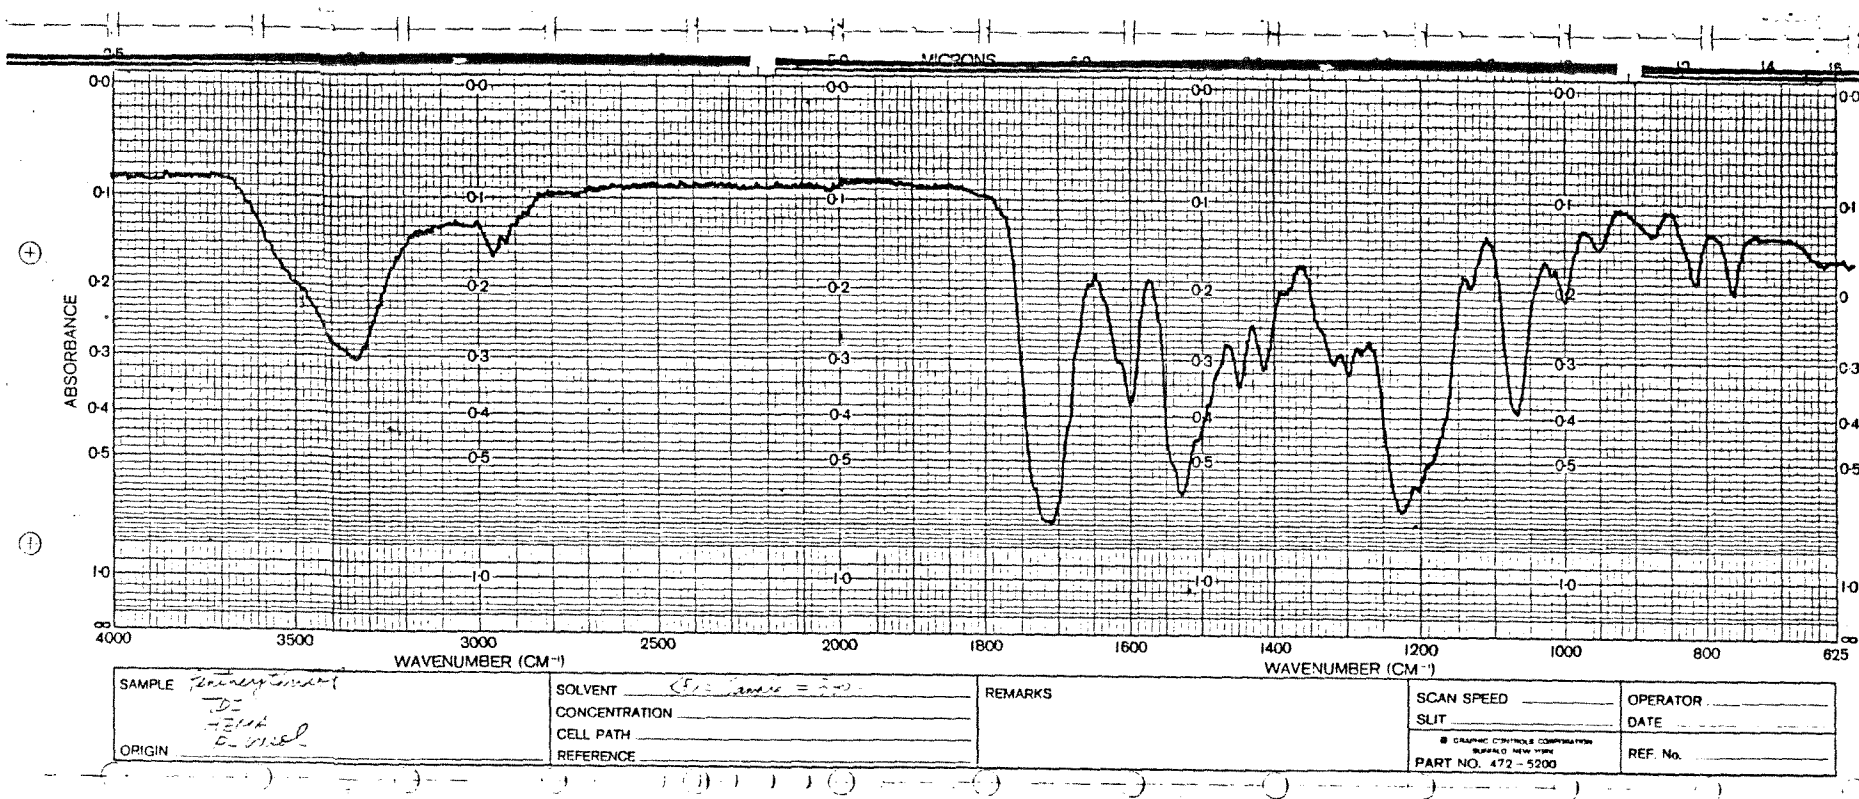


Fig. 6 IR Spectra of Pentaerythritol-TDI-
HEMA-p-Cresol

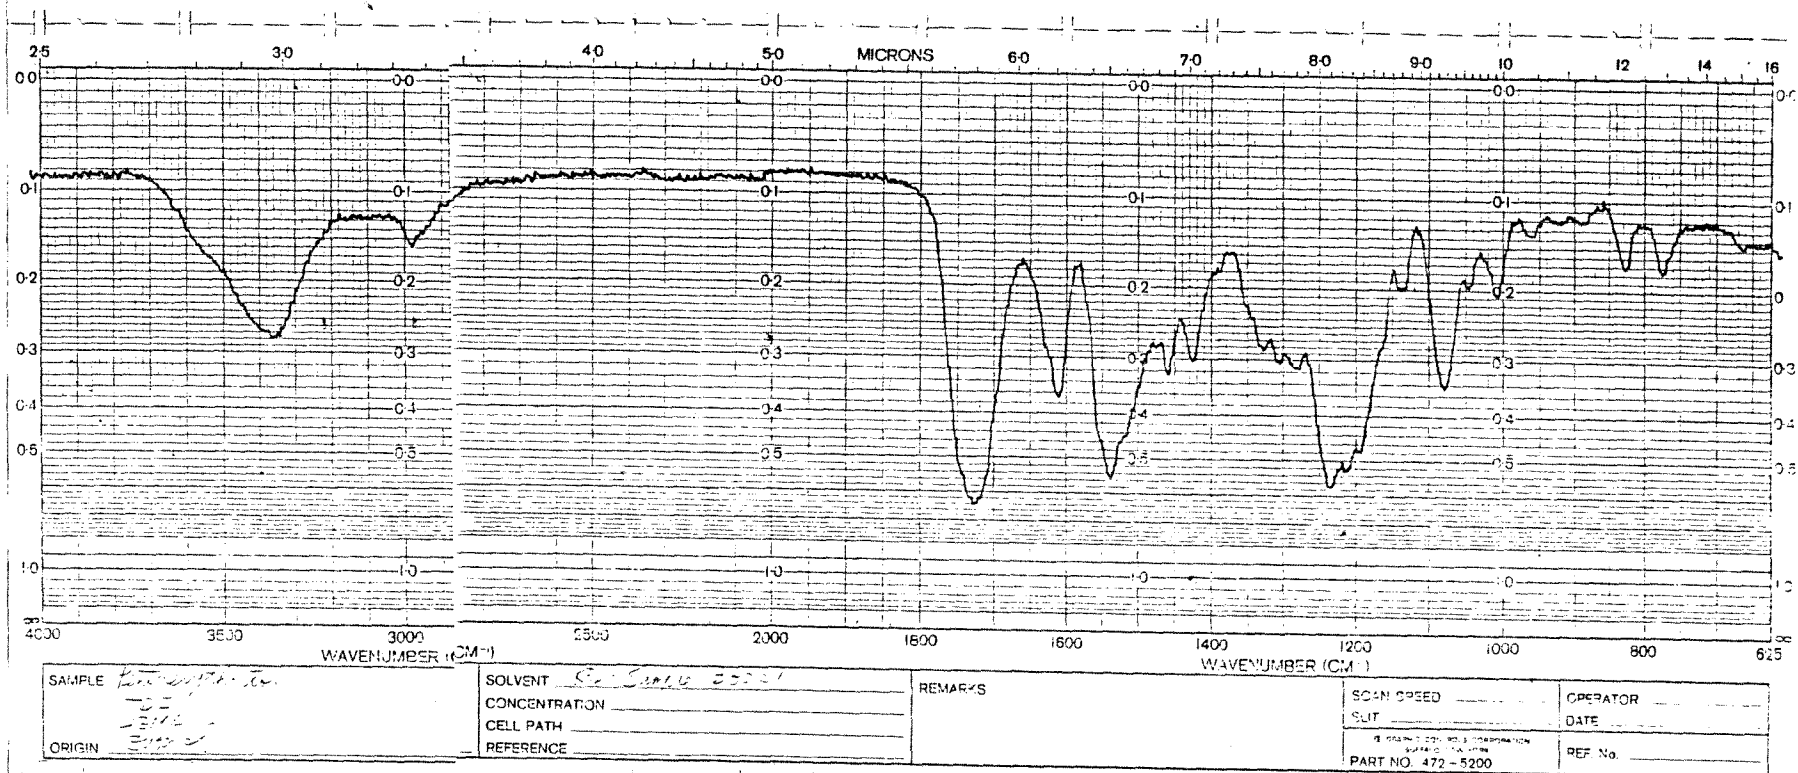


Fig. 7 IR Spectra of Pentaerythritol-TDI-
HEMA-Eugenol

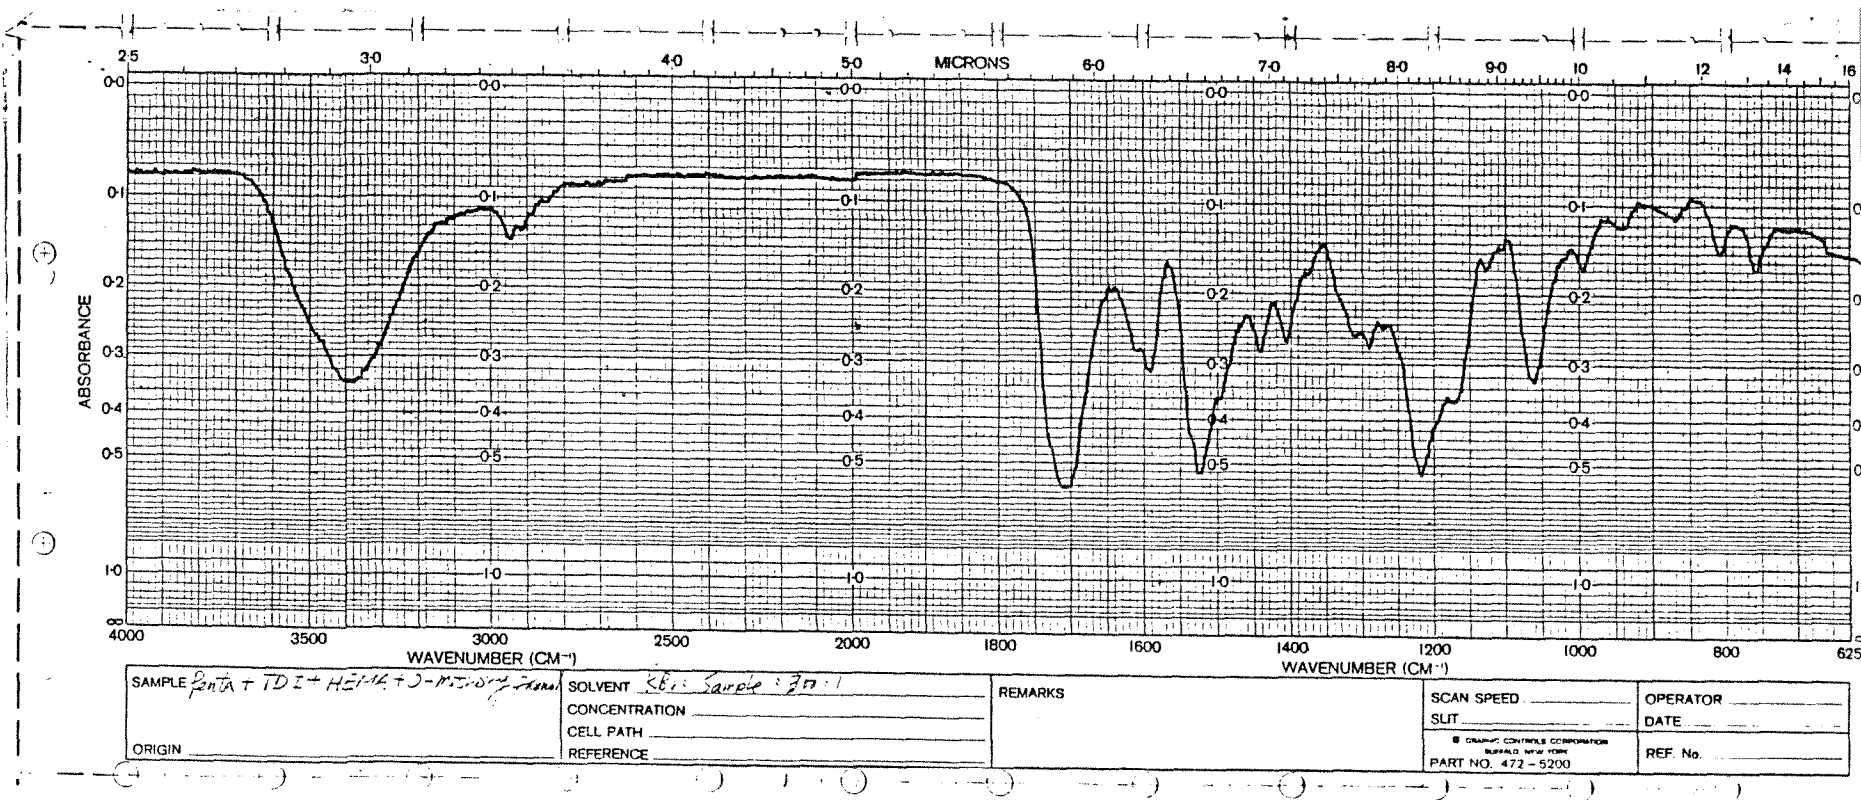


Fig. 8 IR Spectra of Pentaerythritol-TDI-
HEMA-o-Methoxyphenol


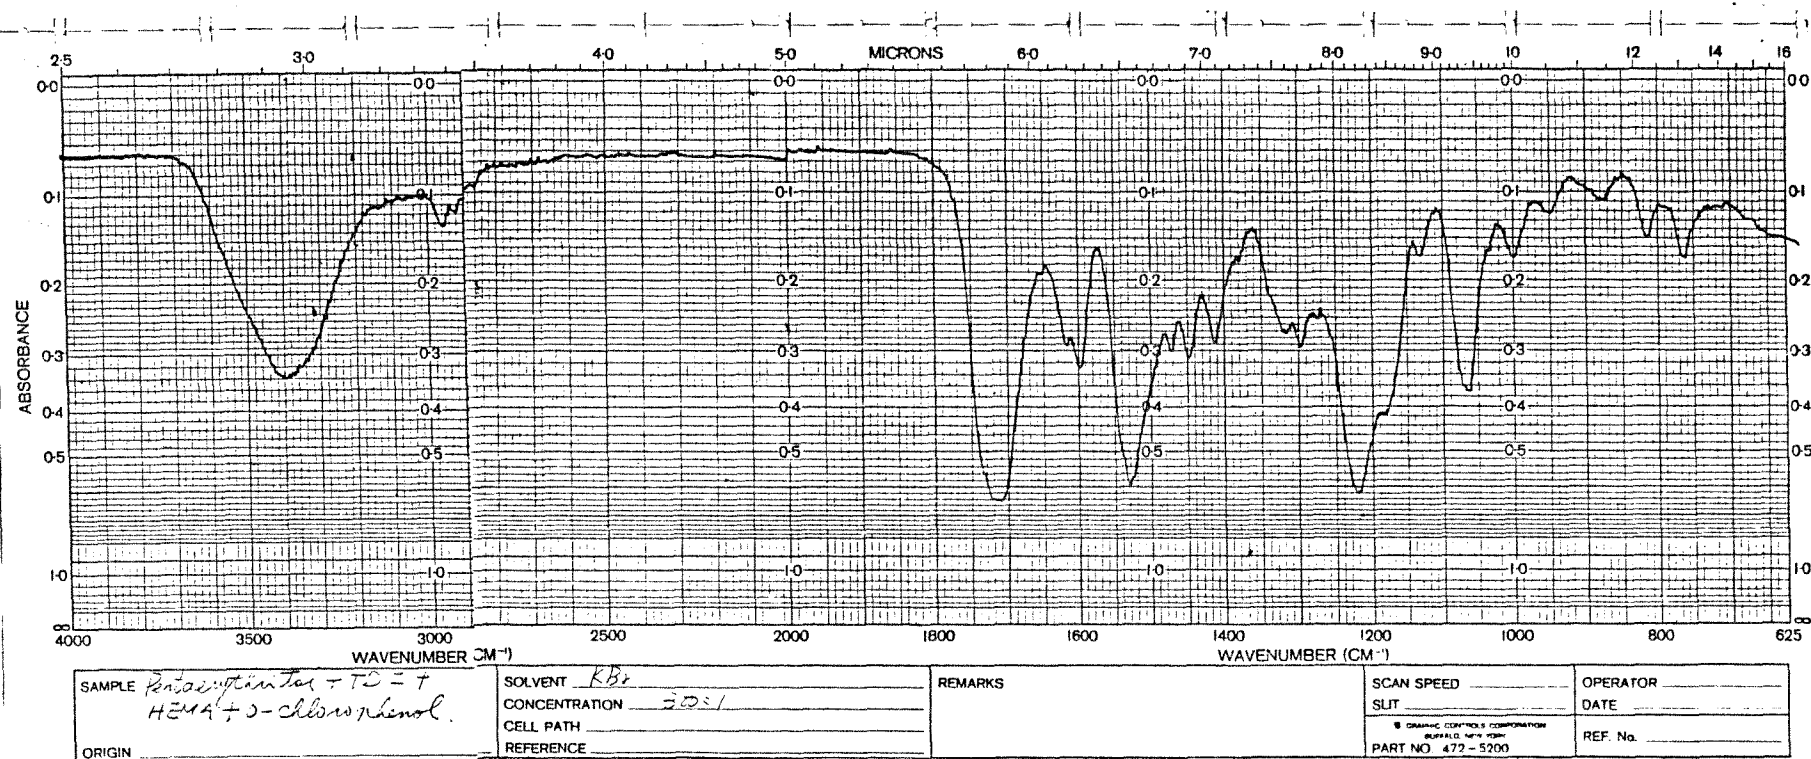


Fig. 9 IR Spectra of Pentaerythritol-TDI-
HEMA-o-Chlorophenol.

radio lab, California


instrument division

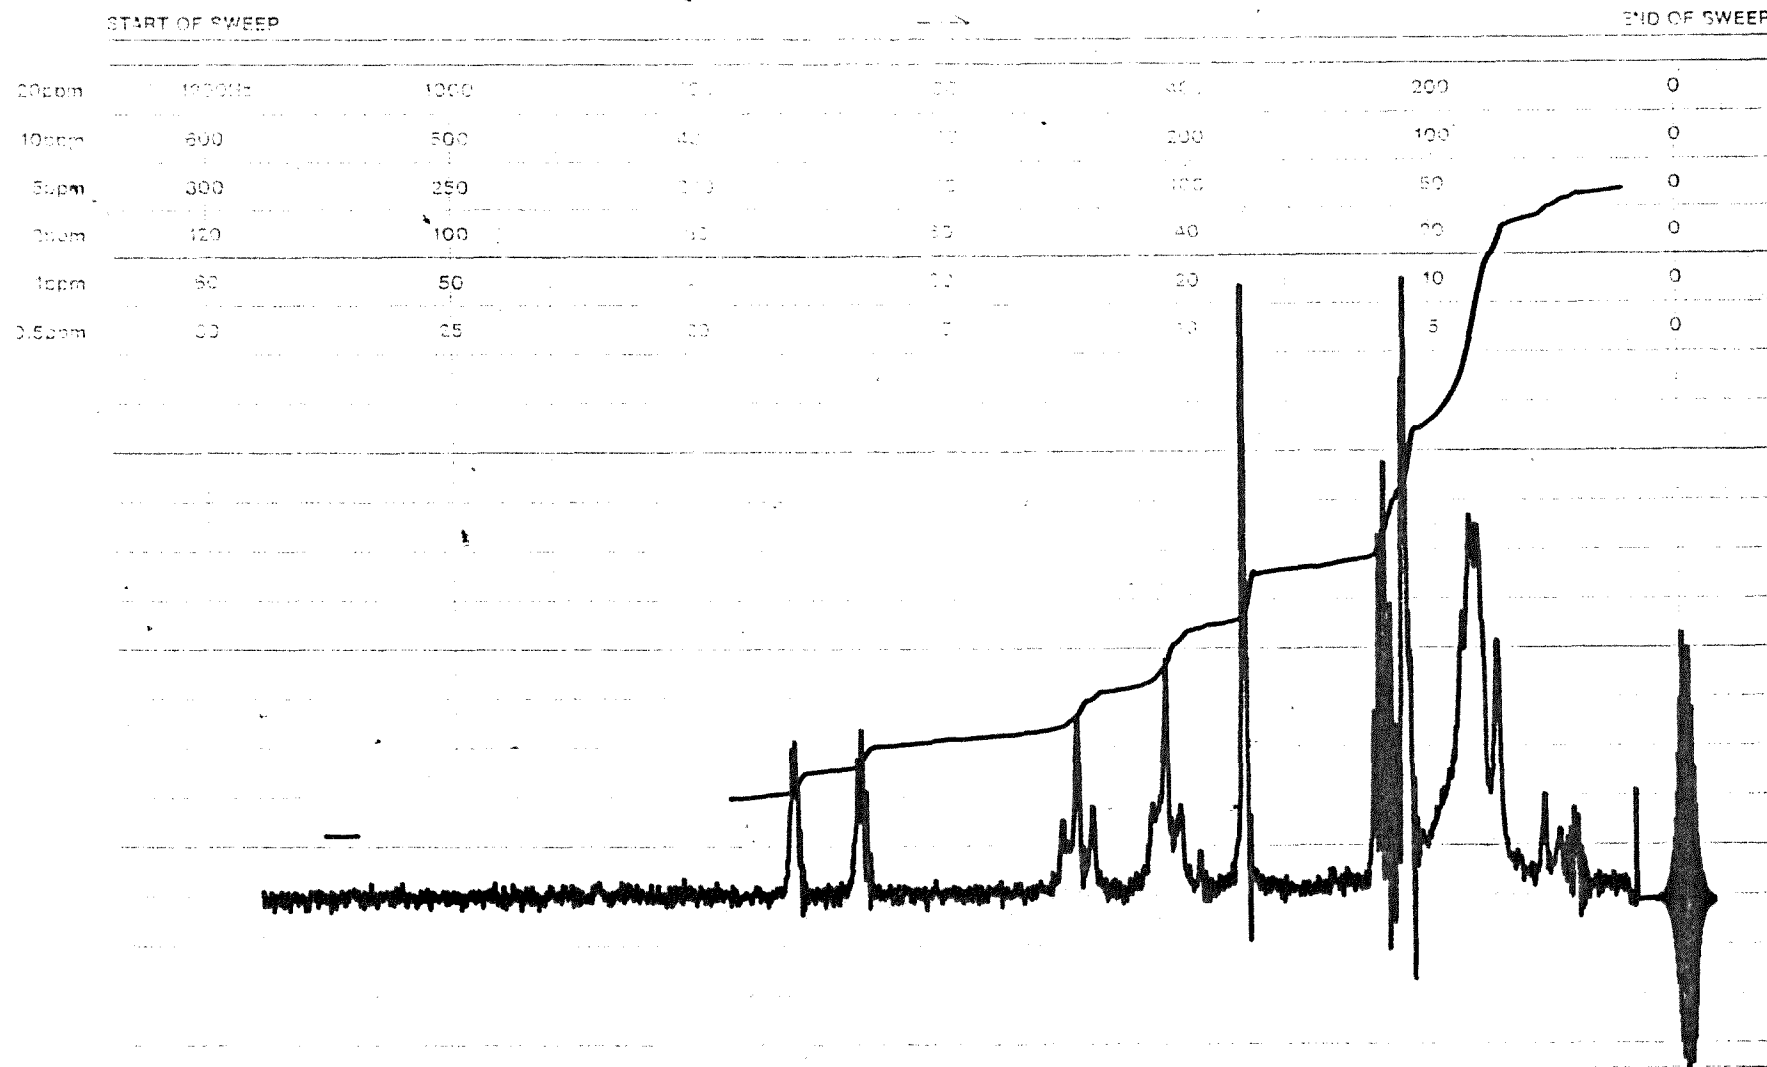

1.6. Hexanol
+ methacrylic
acid

Unsat.
aceton

Fig. 10 NMR Spectra of Hydroxyhexylmethacrylate

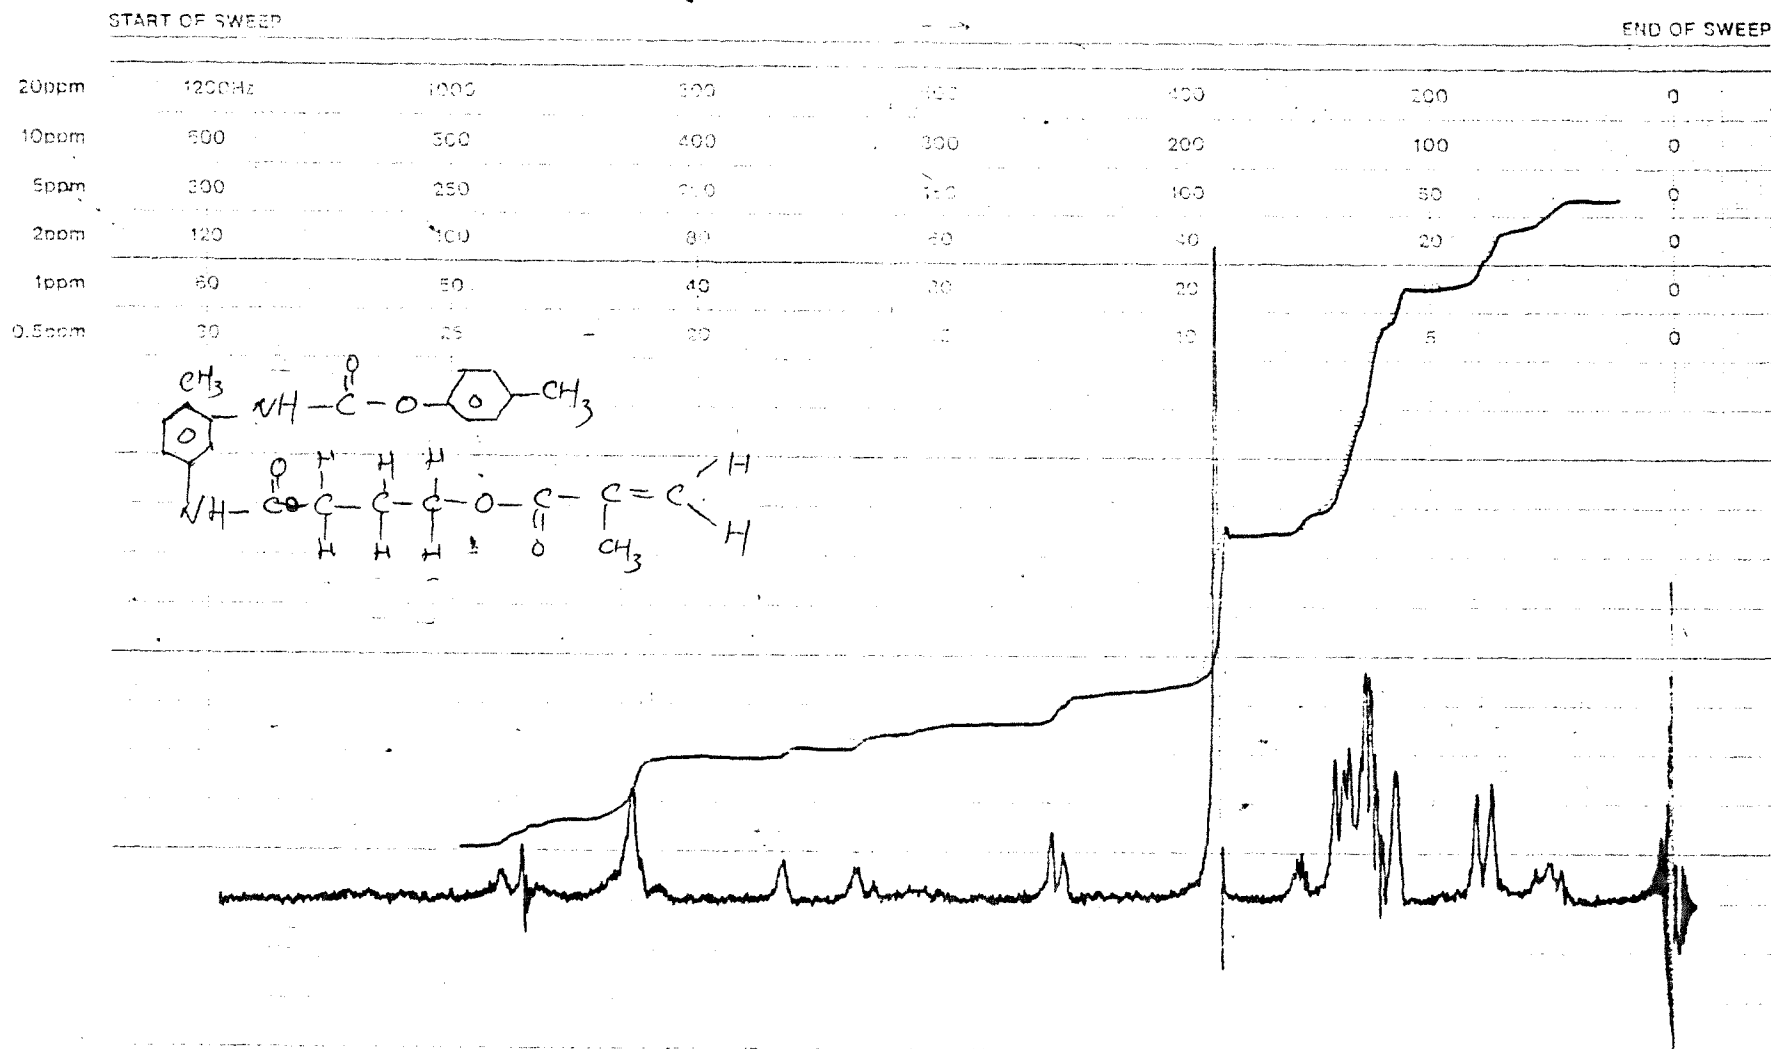

CS-1300 COMPARISON SPECTROMETER

[illegible]

5
10

P-606.
F-circled Blocked

Uien 150

Fig. 11 NMR Spectra of HPMA-TDI-p-Cresol

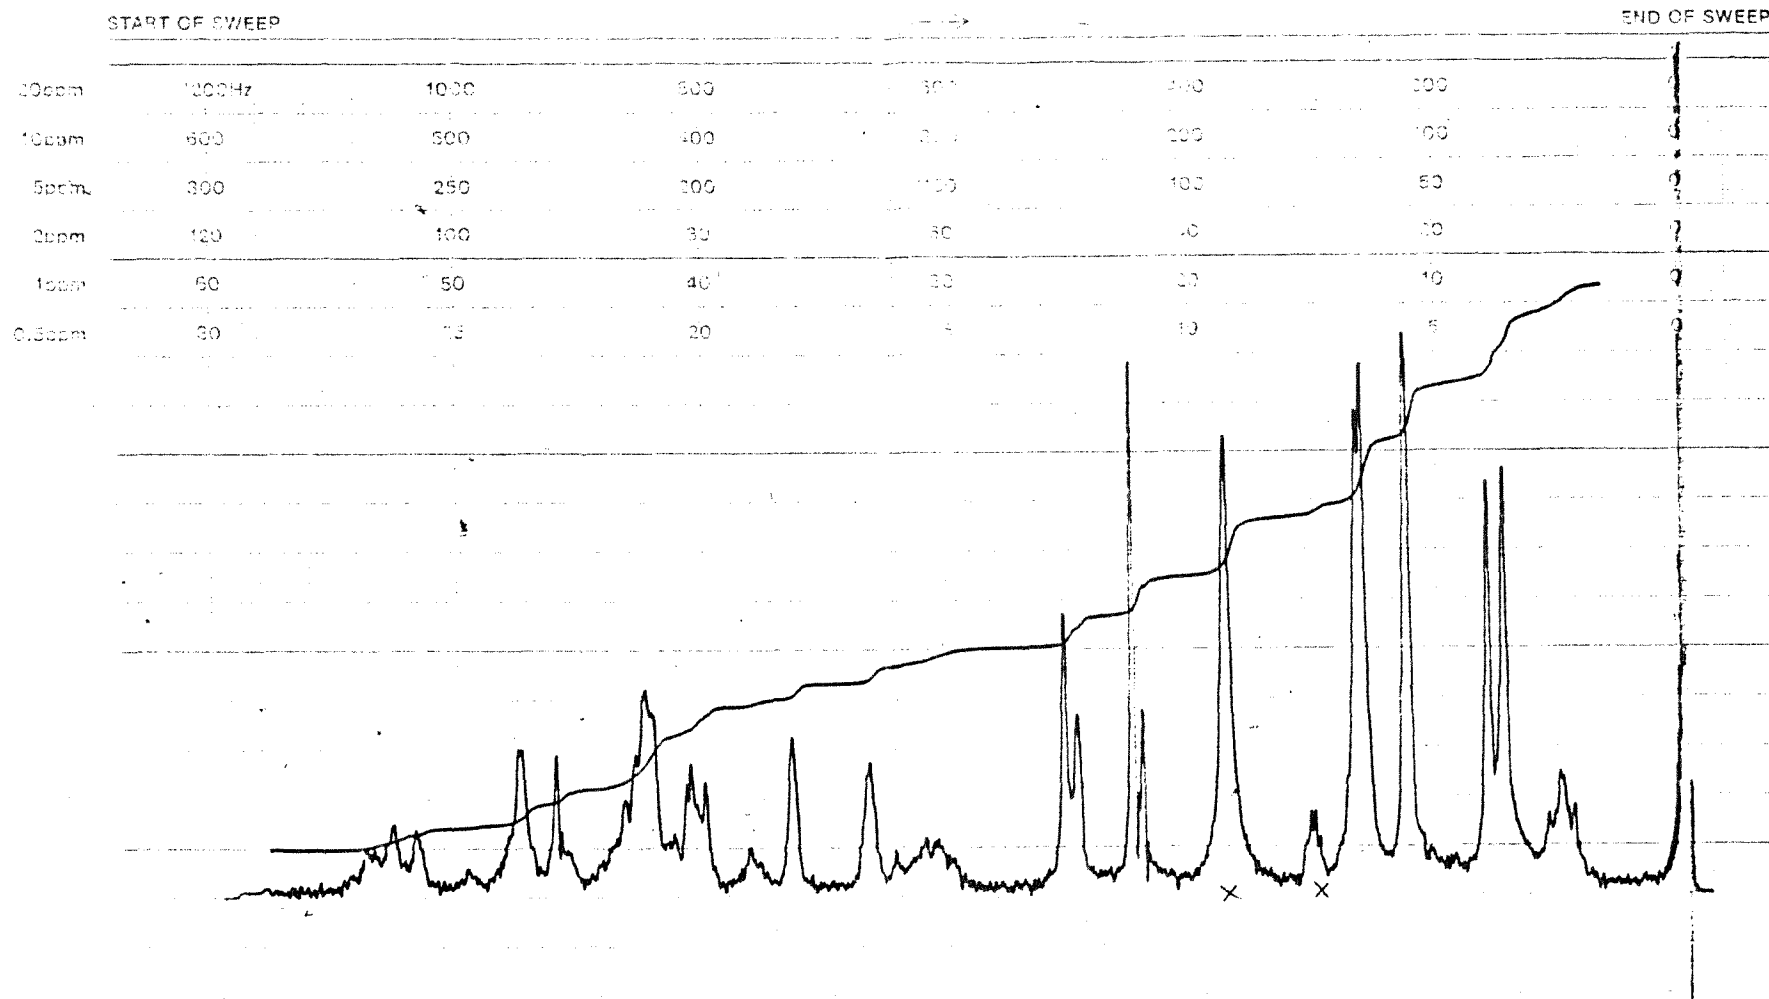


Fig. 12 NMR Spectra of HPMA-TDI-m-Methoxyphenol

P-70.
 m-methoxy
 phenol
 limits

START OF SWEEP

END OF SWEEP

| | | | | | | | |
|--------|--------|------|-----|----|-----|-----|---|
| 20ppm | 1000Hz | 1000 | 500 | 50 | 400 | 200 | 0 |
| 10ppm | 500 | 500 | 400 | 30 | 200 | 100 | 0 |
| 5ppm | 200 | 250 | 200 | 15 | 100 | 50 | 0 |
| 2ppm | 120 | 100 | 80 | 50 | 40 | 20 | 0 |
| 1ppm | 60 | 50 | 40 | 30 | 20 | 10 | 0 |
| 0.5ppm | 30 | 25 | 20 | 15 | 10 | 5 | 0 |



EM-360 60 MHz NMR SPECTROMETER

CONCENTRATION 0.01
 TEMPERATURE 105
 SOLVENT 0.05
 PULSE PROGRAM 4000
 GAIN 10
 TMS
 Pentaerythritol + TDI
 Unisol
 DATE 7/10/84


Fig. 13 NMR Spectra of Pentaerythritol-TDI

Carbon Instrument Division Palo Alto, California

START OF SWEEP

END OF SWEEP

| | | | | | | | |
|--------|--------|------|-----|-----|-----|-----|---|
| 20ppm | 1200Hz | 1000 | 800 | 600 | 400 | 200 | 0 |
| 10ppm | 600 | 500 | 400 | 300 | 200 | 100 | 0 |
| 5ppm | 300 | 250 | 200 | 150 | 100 | 50 | 0 |
| 2ppm | 120 | 100 | 80 | 60 | 40 | 20 | 0 |
| 1ppm | 60 | 50 | 40 | 30 | 20 | 10 | 0 |
| 0.5ppm | 30 | 25 | 20 | 15 | 10 | 5 | 0 |

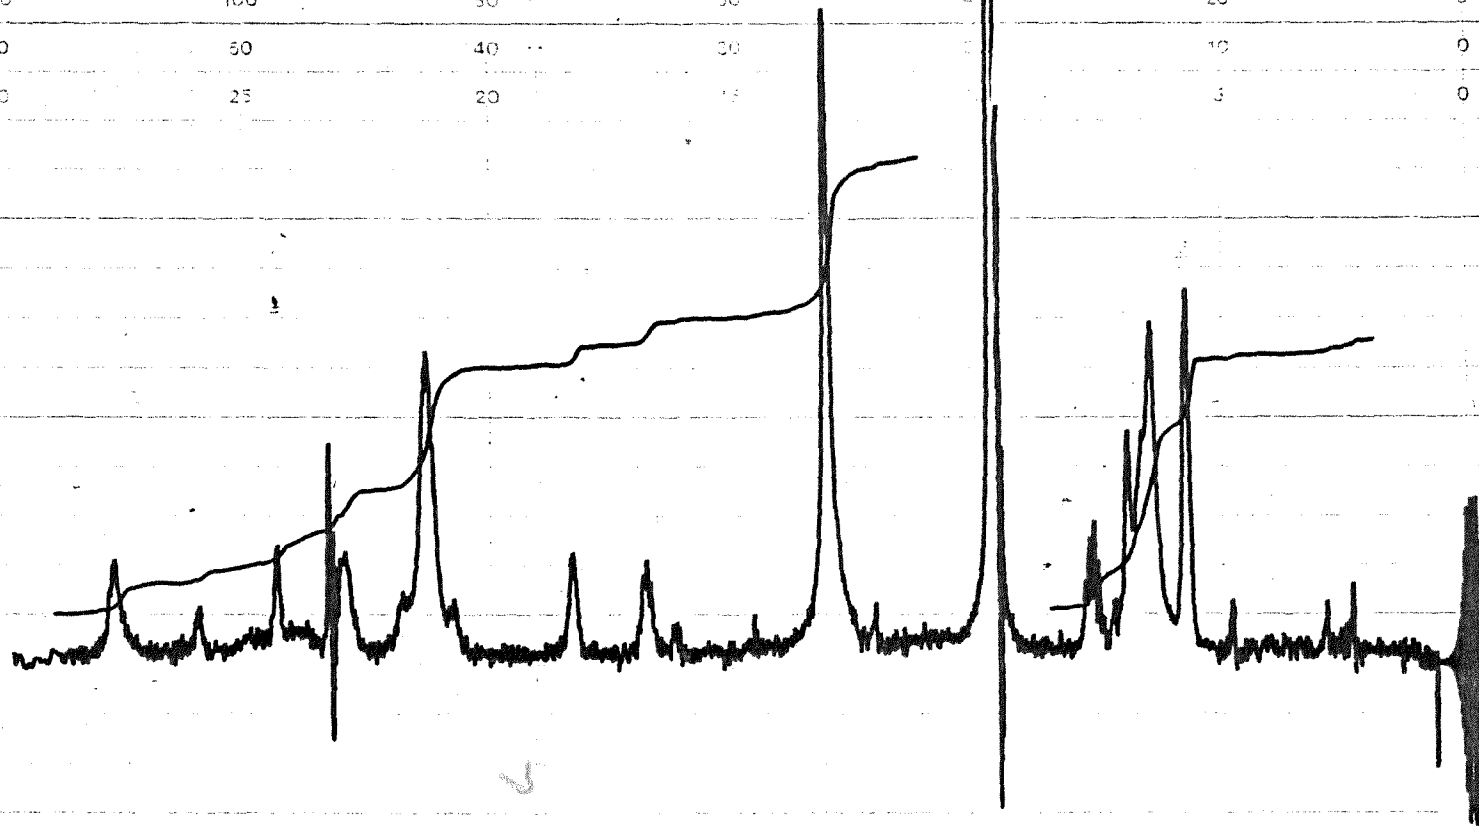

EM-360 60 MHz NMR SPECTROMETER

0.01
0.05
0.05

5
10
0

p-cresol blocked HEMA-PE-T.
#1
unisol


Fig. 14 NMR Spectra of Pentaerythritol-TDI-HEMA-p-Cresol

San Jose, California

Instrument Division

START OF SWEEP

END OF SWEEP

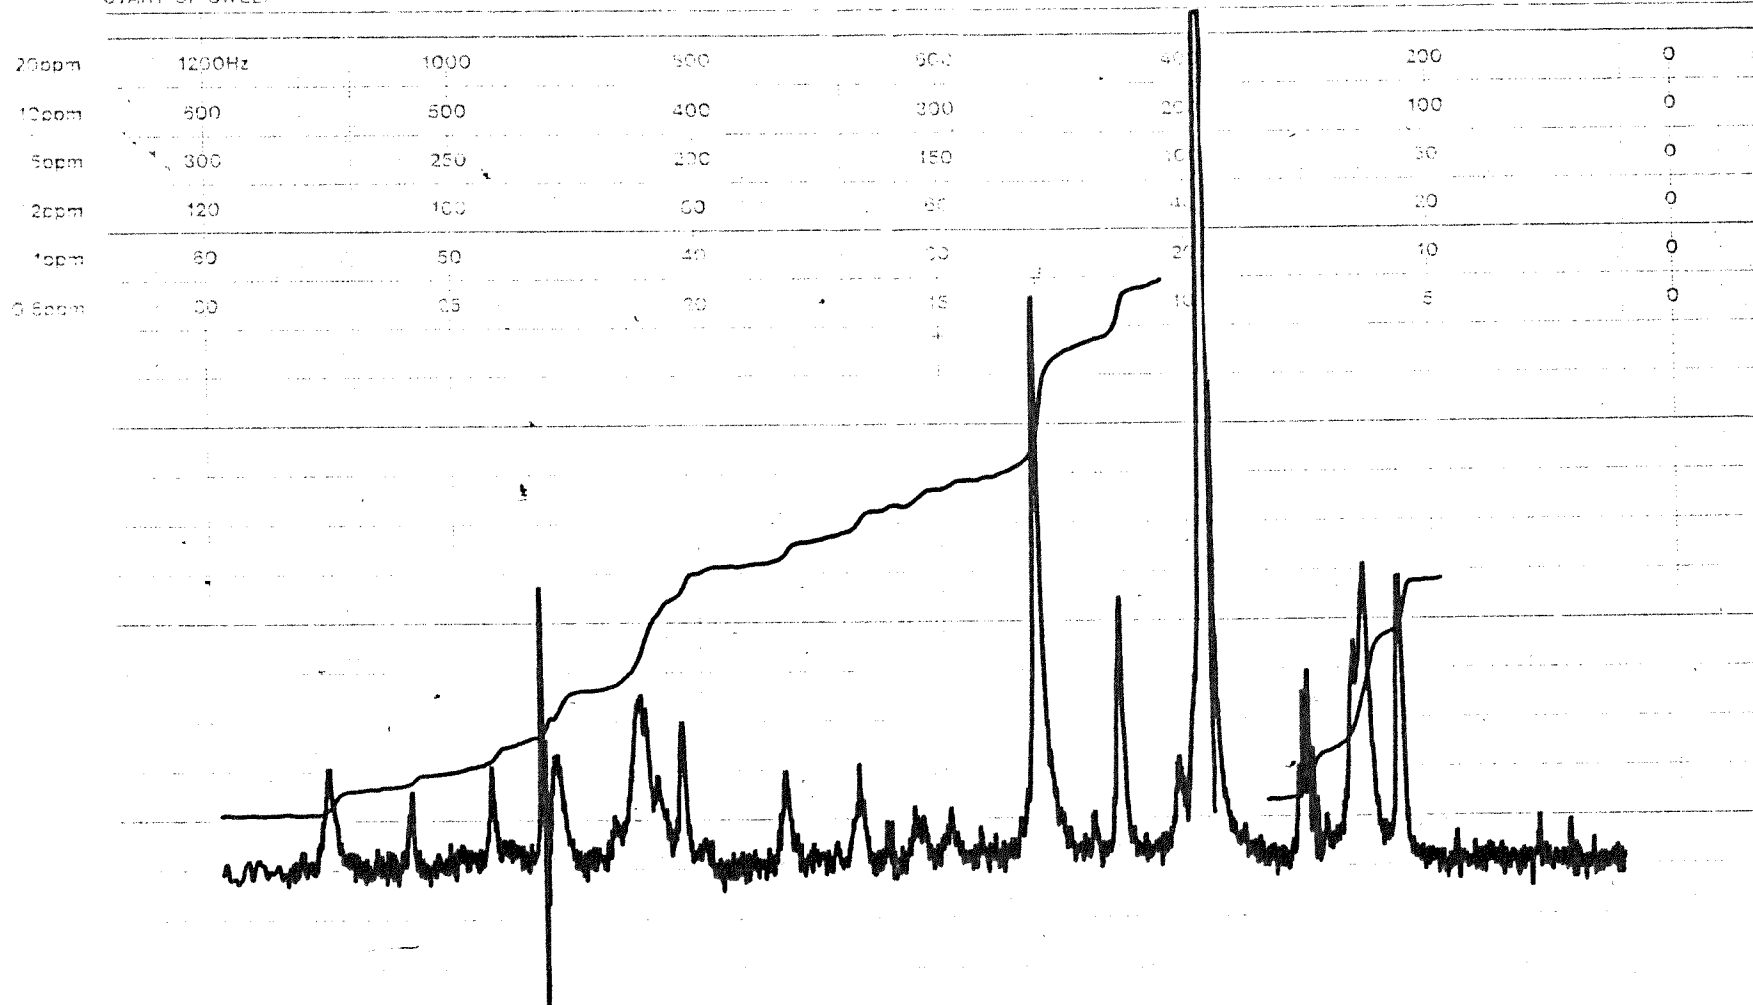

EM-360 60 MHz NMR SPECTROMETER

8000
105
105
10

#2 eugenol blocked HEMA-PE-T₀
united

Fig. 15 NMR Spectra of Pentaerythritol-TDI-HEMA-Eugenol

START OF SWEEP

END OF SWEEP

| | | | | | | | |
|--------|--------|------|-----|-----|-----|-----|---|
| 20ppm | 1200Hz | 1000 | 800 | 600 | 400 | 200 | 0 |
| 10ppm | 600 | 500 | 400 | 300 | 200 | 100 | 0 |
| 5ppm | 300 | 250 | 200 | 150 | 100 | 50 | 0 |
| 2ppm | 120 | 100 | 80 | 60 | 40 | 20 | 0 |
| 1ppm | 60 | 30 | 40 | 30 | 20 | 10 | 0 |
| 0.5ppm | 30 | 25 | 20 | 15 | 10 | 5 | 0 |

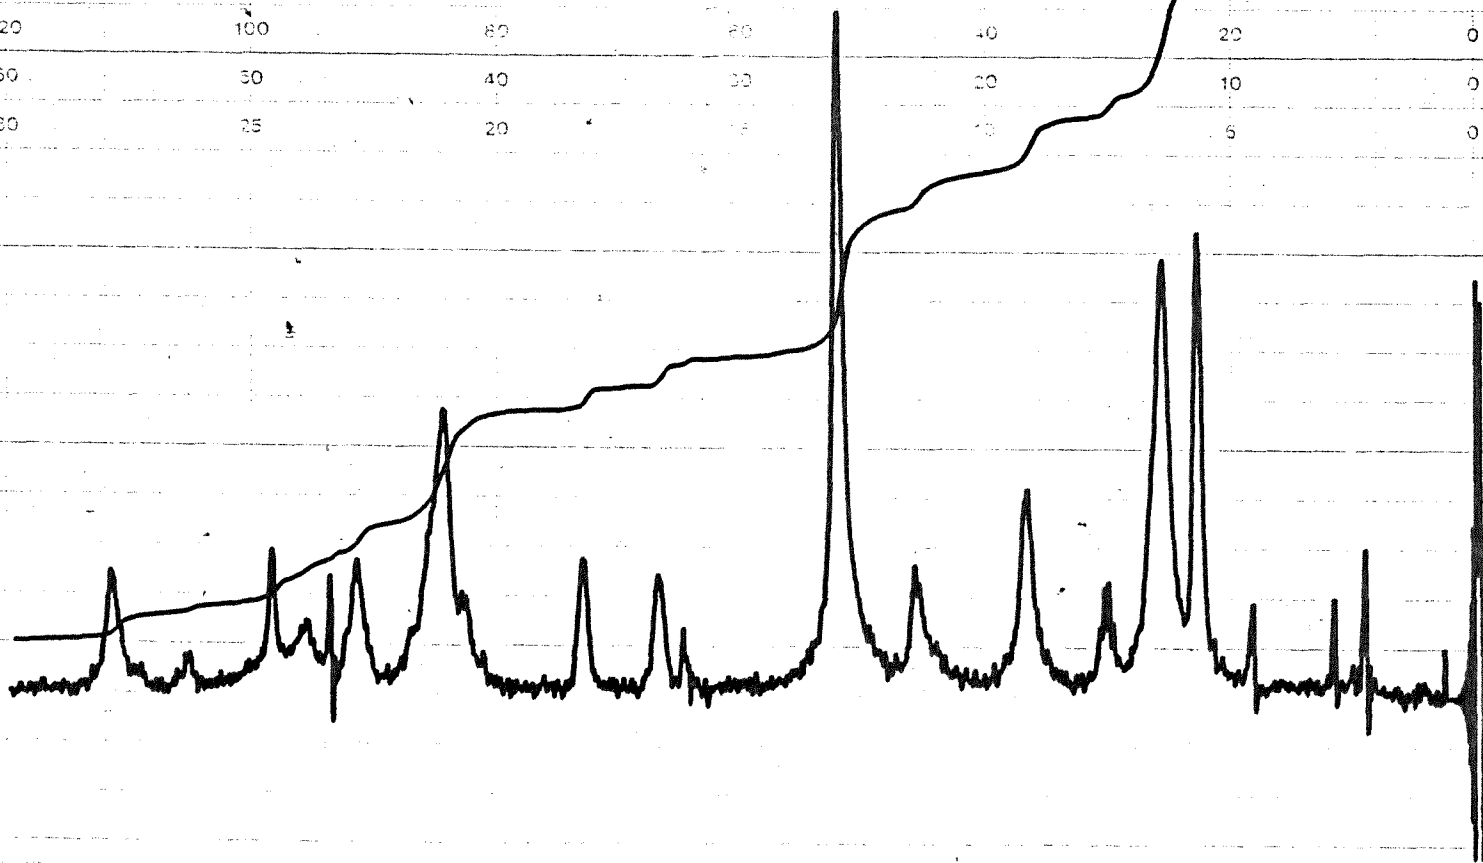


Fig. 16 NMR Spectra of Pentaerythritol-TDI-HEMA-o-Methoxyphenol

2X 0
.01

7000

5

10

0

TMS

Pentaerythritol

TDI

HEMA


o-methoxyphenol

Unisol

START OF SWEEP

END OF SWEEP

| | | | | | | | |
|--------|--------|------|-----|-----|-----|-----|---|
| 20ppm | 1200Hz | 1000 | 800 | 600 | 400 | 200 | 0 |
| 10ppm | 600 | 500 | 400 | 300 | 200 | 100 | 0 |
| 5ppm | 300 | 250 | 200 | 150 | 100 | 50 | 0 |
| 2ppm | 120 | 100 | 80 | 60 | 40 | 20 | 0 |
| 1ppm | 60 | 50 | 40 | 30 | 20 | 10 | 0 |
| 0.5ppm | 30 | 25 | 20 | 15 | 10 | 5 | 0 |

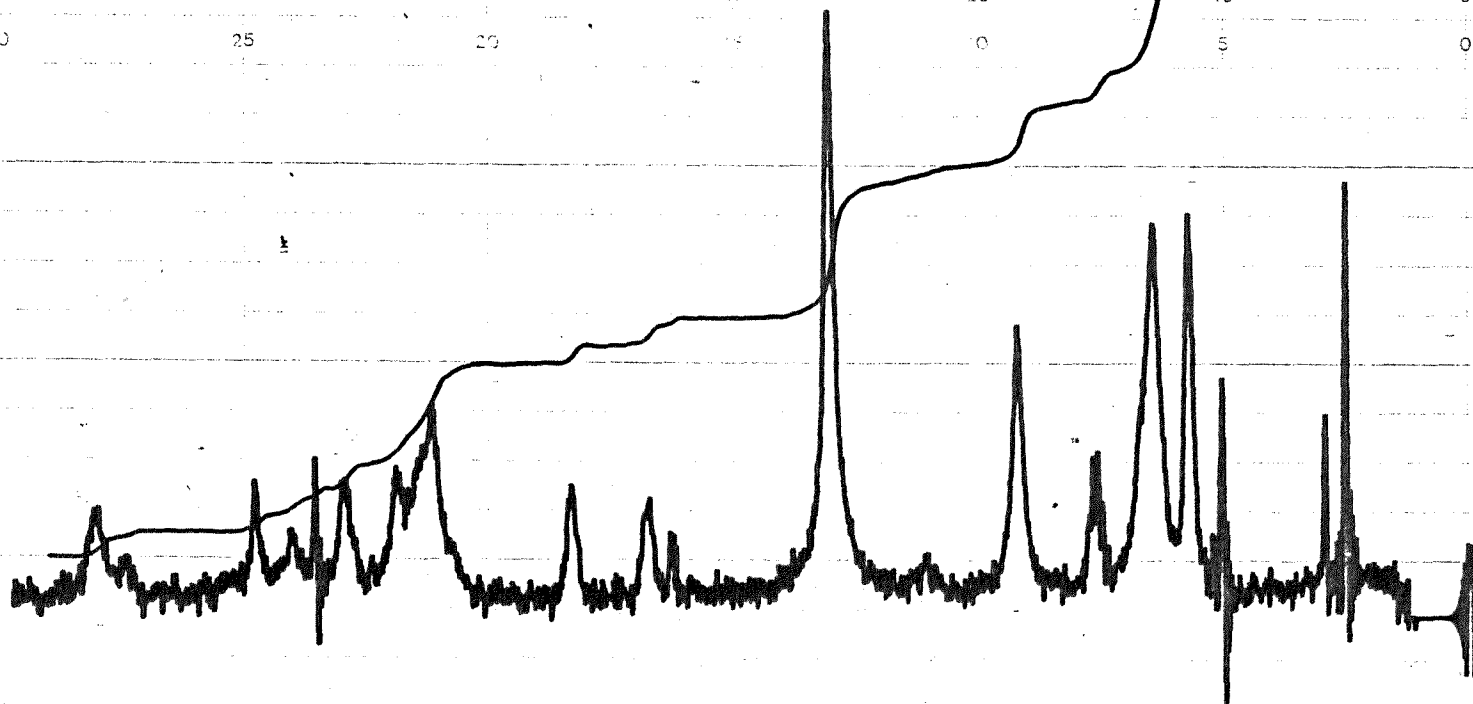

0 10 20 30 40 50 60 70 80 90 100 110 120 130 140 150 160 170 180 190 200 210 220 230 240 250 260 270 280 290 300 310 320 330 340 350 360 370 380 390 400 410 420 430 440 450 460 470 480 490 500 510 520 530 540 550 560 570 580 590 600 610 620 630 640 650 660 670 680 690 700 710 720 730 740 750 760 770 780 790 800 810 820 830 840 850 860 870 880 890 900 910 920 930 940 950 960 970 980 990 1000

TDI + Pentaerythritol
+ HEMA + o-chlorophenol

Fig. 17 NMR Spectra of Pentaerythritol-TDI-HEMA-o-Chlorophenol

RESULT AND DISCUSSION

The use of TMP-TDI adduct as the main body of dental adhesives had been developed completely in previous attempts. There are three hydroxyl groups in TMP available for reaction with isocyanate groups in TDI. After reacting with hydroxyl groups in TMP, it was expected that an unreacted isocyanate group was left on each TDI for the next step, the reaction with blocking agent or HEMA. Therefore, three opportunities for bonding exist in the dental adhesive molecules, most probably two bonds to dentin and one to filling material or vice versa.

In order to maximize both the bonding to dentin and copolymerization to the resin, a compound with four hydroxyl groups, pentaerythritol, was selected in this study as the main body of the dental adhesives.

The chemical principle for the reaction of pentaerythritol and TDI is the same as that of TMP-TDI, but the system for preparing pentaerythritol-TDI adduct is quite different from that of TMP-TDI. In the case of pentaerythritol-TDI adduct, the powdered pentaerythritol was directly added to the solution of TDI and p-dioxane instead of dissolving into dry THF solvent. Moreover, a polar solvent, p-dioxane, was used to dissolve the pentaerythritol-TDI adduct.

33

As the previous study found, the TDI may participate in the reaction of the ortho as well as the para isocyanate group even though the reactivity ratio of para isocyanate

to ortho isocyanate in TDI is about twelve to one in favor of para isocyanate at room temperature. In this way one TDI could attach to two molecules of pentaerythritol; the other branches pentaerythritol could react with different TDIs at ortho, para, or both sites. This sequence could go on and produce oligomers and/or polymers. Hence the tendency to increase the ortho position reactivity should be reduced as much as possible so that the formation of oligomers and /or polymers can be reduced drastically.

First, the reaction should be maintained below room temperature. It was known that at ³⁷90°C para and ortho isocyanate of TDI have the same reactivity. In other words, the relative reactivity of ortho isocyanate would be increased at elevated temperatures. Due to the exothermic behavior of the reaction and the heat evolved by the high speed stirrer the temperature of the reaction tended to rise as high as 45°C. Thus, it is essential to maintain the temperature below room temperature by using a cooling system to depress the tendency of ortho isocyanate reaction.

Secondly, an excess amount of TDI is necessary to permit all the hydroxyl groups in pentaerythritol to react with para isocyanates on TDI molecules. When a molecule of pentaerythritol in contact with the TDI-dioxane solution it would be surrounded by many TDI molecules. Therefore, the hydroxyl groups would have a low probability of reacting with ortho isocyanates in TDI. Certainly, there are still some reactions between pentaerythritol and TDI at ortho

positions; Using an excess of TDI is to minimize the pentaerythritol reaction with the less favorable ortho isocyanates.


In Table XXVI we reported that the result of the element analyses of the pentaerythritol-TDI adduct shows excellent agreement between the theoretical and observed values. Also, the infrared spectrum shows in Fig 5 the presence of a strong peak at 2250 cm^{-1} , which indicates that free isocyanates are still available on the pentaerythritol-TDI adduct.

For the use of dental adhesives, the monomers must not only react with dentin but also with the filling material. The desired dental adhesives in this study are that in which two of the four isocyanate groups in pentaerythritol-TDI are reacted with HEMA, the other two with blocking agents. Therefore, equal molar quantities of HEMA and blocking agent, were used to react the pentaerythritol-TDI adduct; both compounds were introduced simultaneously. HEMA contains aliphatic hydroxyl group, therefore, reacts more rapidly with the free isocyanate groups than do the phenolic blocking agents such as p-cresol, o-chlorophenol etc. Thus, an even larger amount of phenolic blocking agent was used in the reaction in order to increase the chance of blocking agents reacting with pentaerythritol-TDI adduct. At the beginning, 6% excess of HEMA and about 20% excess of phenolic blocking agents were added to the blocking reaction. After 7 days, the IR showed a peak for isocyanate functional group indica-

ting that the reaction was incomplete. Farfhad's³³ study showed that only 6% excess HEMA is sufficient to block a TMP-TDI in seven days. Therefore, the delay in our blocking reaction could be due only to the insufficient reactivity of blocking agents. Thus, after seven days more phenolic blocking agents were added, which resulted in complete reaction.

Blocking by para cresol and HEMA took nine days. For o-methoxyphenol-HEMA, eugenol-HEMA and o-chlorophenol-HEMA the reaction took 11, 13, and 19 days, respectively. It can be concluded that, in general, increasing the percentage of excess blocking agent results in shorter time for the complete blocking reaction.

Temperature is also a very important factor in the blocking reactions. The experiment shows that the blocking temperature for p-cresol-HEMA is 50°C. However, if this temperature is applied to each of the preparations o-methoxyphenol-HEMA, eugenol-HEMA and o-chlorophenol-HEMA, there were still observed considerable peaks for the isocyanate functional group at 2250 cm⁻¹ even after 20 days. In fact, it is well known that the blocking reaction is a reversible reaction; the forward reaction is a blocking reaction and reverse one is a deblocking reaction.

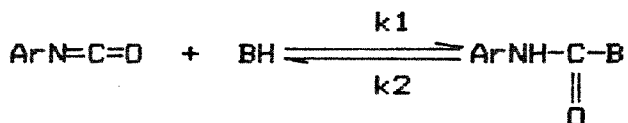

According to the kinetics, the rate of reaction is

proportional to rate constant and concentration. At the beginning, the concentration of blocked product was almost equal to zero, the net reaction is favorable the forward reaction. But after the reaction proceeds for some time, the concentration of blocked product increases, the tendency in favor of forward reaction would gradually change to equilibrium between the forward and reverse reaction. At equilibrium the forward and reverse reaction rates are equal.

At lower temperatures the forward reaction was much faster than the reverse one, $k_1 \gg k_2$. As temperature rises, however, the rate constant of reverse reaction would gradually approach that of forward reaction. Therefore, the equilibrium constant, K , becomes smaller and smaller. That is, there is no improvement in the yield of the blocking reaction. Thus, the reverse reaction becomes more obvious so that the absence of free isocyanate peak at 2250 cm^{-1} would never be obtained. In this study, much of time was spent on the search of optimum blocking temperatures. For o-chlorophenol, in general, the blocking reaction must be below 40°C . for the other two cases, eugenol-HEMA and o-methoxyphenol-HEMA, the best temperature was found to be 45°C .

From the temperature data, it is learned that the order of the blocked product stability is p-cresol > eugenol, o-methoxyphenol > o-chlorophenol. If required time for completing blocking reaction is taken into consideration, it would be found that o-methoxyphenol adduct is more stable than eugenol adduct.

All these data support the theory that the required time and temperature for completing the blocking reaction largely depend upon steric and electronic effects in the phenol.

There is no doubt that p-cresol is more reactive to isocyanate groups than o-chlorophenol is, because the methyl group in p-cresol is an electron-releasing factor, unlike the case of electron-withdrawing chlorine in o-chlorophenol. For the methyl group in p-cresol and the methoxy group in o-methoxyphenol from the view point of electron releasing effect, there is no significant difference between both components. But if the steric effect is taken into consideration, it becomes obvious that the para-position substituted compound is more reactive than the ortho-position. Theoretically, the alkene group in eugenol decreases the reactivity of eugenol, but the alkane group can make up for the reduction of reactivity due to alkene group. Hence, it was expected that the reactivity of eugenol and o-methoxyphenol would be almost the same. In fact, the o-methoxyphenol blocked the pentaerythritol-TDI adduct more easily than eugenol did.

Tables XXIII-XXX refer to the elemental analysis for each monomer being made in this study. It can be seen from these tables that the observed values do not agree perfectly with the theoretical values for 50% HEMA and 50% blocking agent. Instead, the observed values match the theoretical values, e.g. for p-cresol, 70% HEMA and 30% p-cresol. In

addition, the NMR spectrum (Fig 10-17) also support the elemental calculations in Table XXIII and XXX. For example, in the case of o-methoxyphenol, the result of the integration of methoxy peak in o-methoxy phenol is about one third of the integration of methyl peak in HEMA. This proves the substitution of o-methoxyphenol is one third of the substitution of HEMA, 25% o-methoxyphenol and 75% HEMA as shown on Table XXIX.

A dental adhesive with 70% HEMA and 30% p-cresol attached to four isocyanate groups, for example, means 2.8 positions were attacked by HEMA and 1.2 positions were attacked by p-cresol. From these numbers, it can be assumed that the final monomers being obtained in this study could be a mixture of the following five monomers.

1. all four isocyanates of the adduct react with HEMA molecules.
2. all four isocyanates of the adduct react with the phenolic blocking agent molecules.
3. Three isocyanates of the adduct react with HEMA molecule and the fourth isocyanate reacts with the phenolic blocking agent.
4. Three isocyanates of the adduct react with phenolic blocking agents while the fourth isocyanate reacts with HEMA molecules.
5. Two isocyanates of the adduct react with HEMA molecules while the other two isocyanates react with phenolic blocking agent.

The monomers prepared through this work are intended for suitable adhesive tests. Slices of human teeth were obtained from the clinics of the New Jersey Dental School. As the distance from the tooth surface to the pulp increases the protein content increases. The slices of teeth cutted from the same tooth may have different protein contents. Generally, the tooth slices with a larger amount of protein would have a stronger bonding strength. In our testing, samples were prepared without considering the factor of different protein contents. The testing results are shown in Table XXXI-XXXX. The result on each table indicates a range of values in bonding strength decreases with the increase in reacting time of the sample in water. It suggests that these results may be due to the lack of strength of the dental collagen or the presence of water that reacts with the deblocked isocyanate groups. Samples having longer setting times show a stronger bonding strength by evidenced in the results shown on Table XXXII and XXXIV. However, the bonding strengths shown on Table XXXIII and XXXVI seem unrealistic because the bonding strength of the sample stored in water for 336 hours is stronger than that of stored for 240 hour. In fact, the testing results shown in Table XXXI-XXXIII were obtained from the specimen that were via a new batch of NNDMPT. As expected, the monomer blocked by o-chlorophenol has a stronger bonding strength than of blocked by p-cresol and the o-chlorophenol blocking monomers are easier to be deblocked to release more free isocyanate groups.

In fact, we found that there are two main influencing factors on bonding strength. One is the freshness of PMMA-MMA dough. the other is the homogeneity of the dough. The PMMA-MMA must keep under nitrogen atmosphere and stored in refrigerator before use it; otherwise it will turn hard due to polymerization and becomes impossible to be applied to the dental adhesive layer coated on the dentin. Even if the dough prepared from partially polymerized PMMA-MMA, the bonding strength are still low. Therefore, we think the freshness and through mixing of the dough in a short time are very important. The degree of polymerization is a function of reaction time. At longer time there is less double bonds in PMMA-MMA mixture to react with the HEMA double bonds in the adhesives. As a result, the bonding is weakened. Furthermore, as the degree of polymerization of PMMA-MMA mixture increases, the viscosity of the mixture also increases. the increase in viscosity makes it rather difficult to stir and consequently results in a non uniform mixture.


The increase in bonding strength for o-chlorophenol and p-cresol is a significant improvement over the previous studies. It believed that a more hydrophobic adhesive would be less resistant to degradation by water. Therefore, we prepared hydroxyhexylmethacrylate in order to eventually prepare blocked isocyanates containing phenols and a more hydrophobic vinyl monomer

CONCLUSION


Although the dental adhesive made in this study was only with 20% o-chlorophenol, rather than the expected 50% o-chlorophenol, an impressive mean bonding strength of 2400 psi was obtained. It is believed that a dental adhesive with 50% o-chlorophenol substitution will greatly increase the bonding strength, because it increases the chance of adhesion by a factor of two. In the future study, a dental adhesives with 50% o-chlorophenol would be very desirable. After the bonded specimens were stored in water, tensile loads decreased significantly. As Braden's work⁵³ stated, water can diffuse into acrylic resin and react with isocyanate groups in the dental adhesive to destroy dimensional stability and reduce the bonding strength. Although the application of ethylene glycol dimethacrylate as cross linking agent was not successful, it is worth trying to find other cross linking agents, which will create a three-dimensional polymer.

The significant accomplishments of this research should be followed by a methodical research to establish the mechanism and limits of the capability of these new dental adhesives.

APPENDIX A. The Equipment Set Up For Preparation of The
Pentaerythritol-TDI Adduct

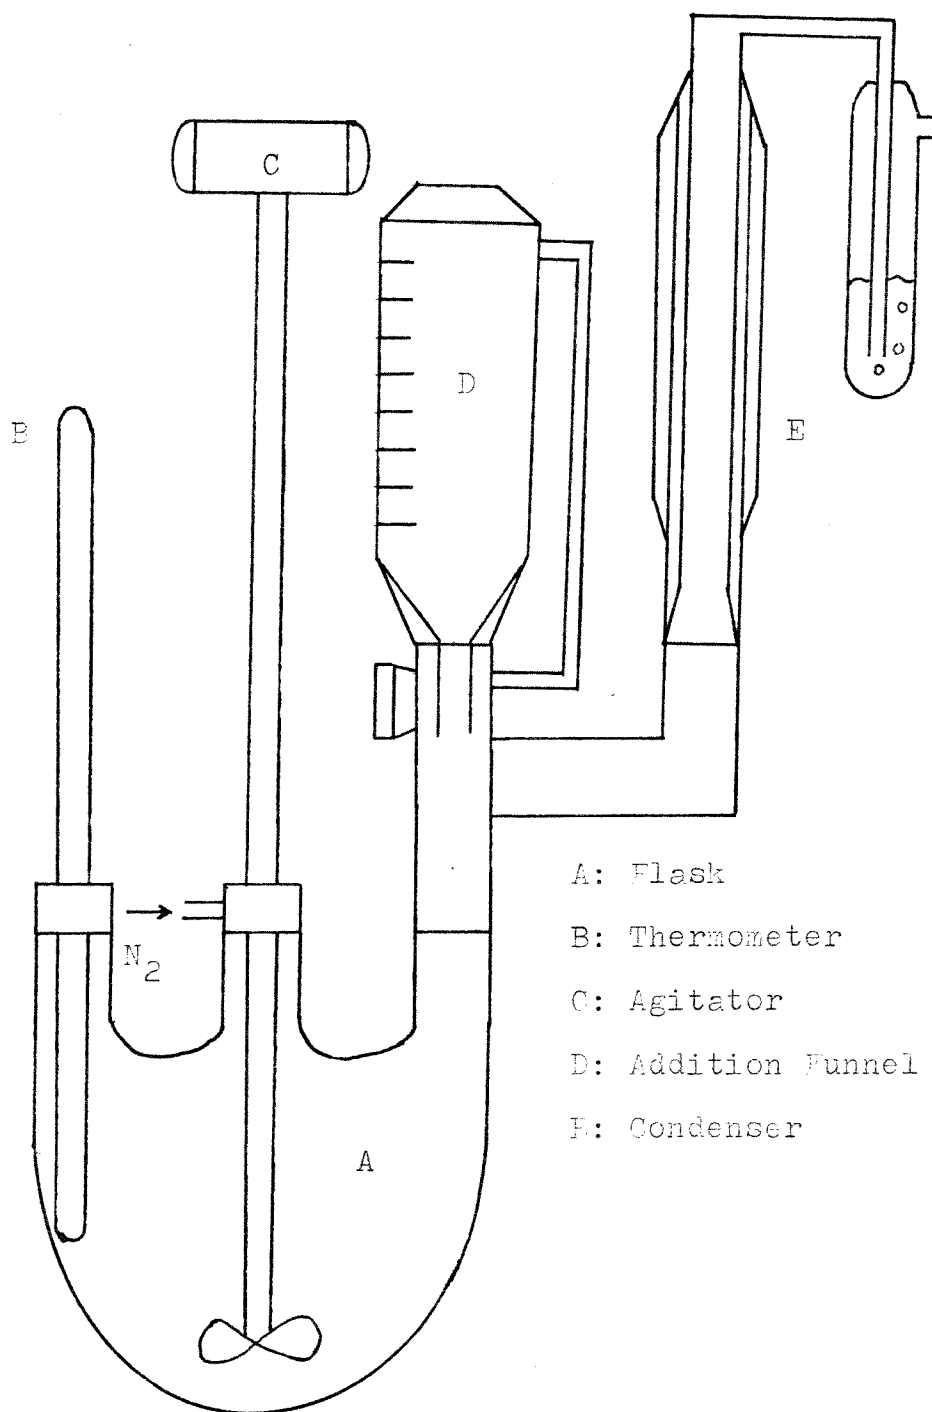

APPENDIX B. The Equipment Set Up For Preparation of The
Hydroxyhexyl Methacrylate

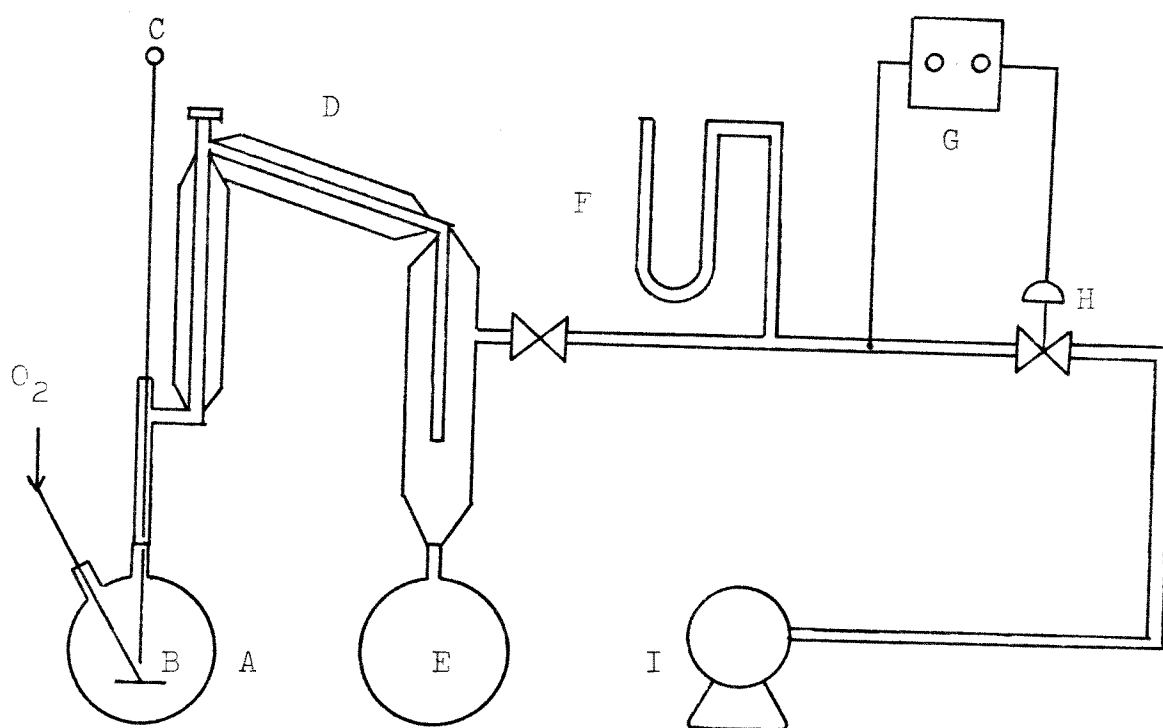

A: Resin Kettle

B: Gas Bubbler

C: Thermometer

D: Condenser

F: Water Collecting Flask


F: Vacuum Indicator

G: Regulator

H: Control Valve

I: Vacuum Pump

APPENDIX C. The Structure of TMP-TDI

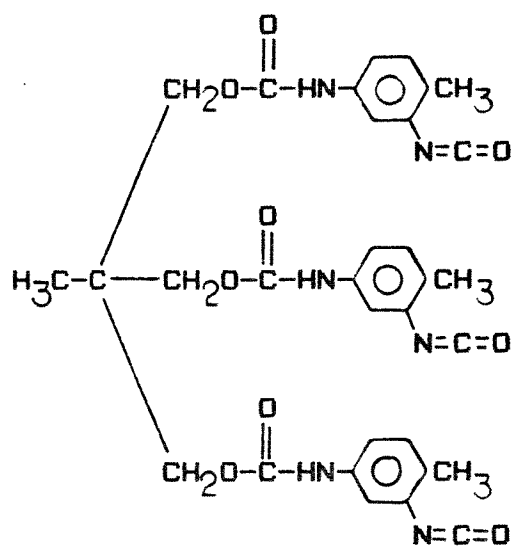

ABBREVIATION

| | |
|---------|-------------------------------|
| DBTDL: | Dibutyltin Dilaurate |
| HEMA: | 2-Hydroxy Ethyl Methacrylate |
| HPMA: | 2-Hydroxy Propyl Methacrylate |
| KBr: | Potassium Bromide |
| MMA: | Methyl Methacrylate |
| NNDMPT: | N,N-dimethyl-p-Toluidine |
| PMMA: | Poly Methyl Methacrylate |
| TDI: | 2,4 Toluene Diisocyanate |
| THF: | Tetrahydrofuran |

BIBLIOGRAPHY

1. Bowen R. L., Cobb E. N., and Rapson J. E., "Adhesive Bonding of Various Materials to Hard Tooth Tissues : Improvement in Bond Strength of Dentin " J. Dent. Res. 61 (9): 1070-1076 1982
2. Munksguard E. C., and Asmussen E., " Bond Strength Between Dentin and Restorative Resins Mediated by Mixtures of HEMA and Glutaraldehyde" J. Dent. Res. 63(8): 1087-1089 1984
3. Munksguard E.C., and Asmussen E., " Bonding of Restorative Resins to Dentin by Means of Methacryloylchloride and Methacryloyl-R-isocyanate" Scand. J. Dent. Res. 91: 153-155 1983
4. Antonucci J. M., Brauer G. M., and Termini D. J., "Iso-cyanate Urethane Methacrylates Derived from Hydroxyethyl Methacrylate" J. Dent. Res. 59(1) : 35-43 1980
5. Buonocore M. G., "Simple Method of Increasing The Adhesive of Acrylic Filling Material to Enamel Surfaces " J. Dent. Res. 34 : 849-853 1955
6. Buonocore M. G., Willeman W. , and Brudevold F., "Report on a Resin Composition Capable of Bonding to Human Dentin Surfaces " J. Dent. Res. 35 : 846-851 1956
7. Rafael L. B., and Everett N. C. , "A Method for Bonding to Dentin and Enamel " JADA Vol. 107 November 1983
8. Stanley H. R. , Going R. E., and Chauncey H. H., "Human Pulp Response to Acid Pretreatment of Dentin and to Composite Restoration " JADA 91(4) :817-825 1975
9. Eriksen H. M., "Pulpal Response of Monkeys to a Composite Resin Cement " J. Dent. Res. 53: 565-570, 1974
10. Bowen R. L., "Surface Active Comonomer and Method of Preparation " US. Patent 3,200,142 (Aug. 10, 1965)
11. Bowen R. L., " Adhesive Bonding of Various Materials to Hard Tooth Tissues: Bonding to Dentin Promoted by a Surface Active Comonomer " J. Dent. Res. 44: 895-902 1965
12. Bowen R. L., " Adhesive Bonding of Various Materials to Hard Tooth Tissues: Bonding to Dentin Improved by Pretreatment and the Use of a Surface active Comonomer " J. Dent. Res. 44: 903-905 1965

13. Bowen R. L., "Adhesive Bonding of Various Materials to Dentin, Enamel, and Fluorapatite Improved by the Use of a Surface Active Comonomer " J. Dent. Res. 44: 906-911 1965
14. Bowen R. L., "Adhesive Bonding of Various Materials to Hard Tooth Tissues : the Effect of a Surface Active Comonomer on Adhesion to Diverse Substrates " J. Dent. Res. 44: 1369-1373 1965
15. Chandler H.H., and Bowen R. L., "Clinical Evaluation of a Radiopaque Composite Restorative Material After Three and One Half years" J. Dent. Res. 52:1128-1137, 1973
16. Asmussen E., and Munksguard E. C., "Bonding of Restorative Resin to Dentin by Means of Methacryloylchloride and Methacryloyl-R-Isocyanate " Scand. J. Dent. Res. 91: 153-155 1983
17. Ramachandrian G. N., "Treaties on Collagen " Vol. 1, Chemistry of Collagen, Academic Press, N. Y. 1967
18. Easton J. E. "Treaties on Collagen" Vol. 1, Chemistry of Collagen, Academic Press, N. Y. 1967
19. Sanders J. H., and Slocombe R. J., " the Chemistry of Organic Isocyanates" Chem. Rev. 43: 203-218 1948
20. Arnold R.G., and Nelson J.A., " Recent Advances in Isocyanate Chemistry" Chem. Rev. 57: 47-76 1957
21. Buonocore M. G., and Casciani C. A., "Synthesis and Properties of Certain Urethanes of Potential Use in Restorative Dentistry" N. Y. State D. J. 35 135-147 1969
22. Wick Z. W., "Blocked Isocyanate "Progress in Organic Coatings 3: 73-99 1975
23. Williams A. J., Chem. Soc., Perkins Trans. II, 808 1972
24. Williams A. J., Chem. Soc., Perkins Trans. II, 1244 1973
25. Frisch L.P. Rumao, and Mickiewicz A.J., J. Paint Technol., 42: (547) 1970
26. Fedoseev M.S. Marehenko G. N., and Kiryandua L. K., Sin. (7) 163 1970; C. A. 75 18232 1971
27. Griffin G. R., and Willwerth L.J., Ind. Eng. Chem. Prod. Res. Develop., 1 265 1962
28. Tartakovskaya A.M., and Blagonravova A.A., Soedin Ser.

B, 12 (1) 84 190 : C. A. 72 110606 1970

- 29 Tartakovskaya A. M., and Blagonravova A.A., Ikh Prinen .,
(6) 1967; C. A. 68 59196 (1968)
30. Tartakovskaya A.M., and Blagonravova A. A., Ikh Prinen .,
(5) 1968: C. A., 70 37331 1969
31. Angeli S. R., Master's Thesis, NJIT 1983
32. Kamdar K., Master's Thesis, NJIT 1983
33. Forohar F. Master's Thesis, NJIT 1984
- 34 Levy J. F., and Kusen U.S. Pat. 3705, 119; C. A. 78 59887
1973
35. Duncan J.S., and Elmer U.S. Pat. 3668, 186; C.A., 77 76117
1972
36. Reilly C. B., and Orchin M., Paper Presented before the
Division of Paint, Plastics and Printing Ink
Chem. A. C. S. Atlantic City ., N.J. Sept. 1956
37. Saunders J.H., and Frisch K.C., Polyurethanes: Chemistry
and Technology Part I 1962. by John Wiley & Sons.
Inc.
- 38 Phillips R. W., "Skinner's Science of Dental Materials"
1973 Seventh Ed. by W.B. Saunders Company
39. Billmeyer F.W., "Textbook of Polymer Science" 1971 Second
Ed. by John Wiley & Sons Inc.
40. Rose E.E., Lal J., and Green R., "Effect of Peroxide,
Amine and Hydroquinone in varying Concentrations
on the Polymerization rate of Polymethyl
Methacrylate Slurries" J. Amer. Dent. Ass. 56
375-381 1958
41. Meltzer H. T., and Tobolsky A. V., ibid 76 5178 1954
42. Stevens M.P., Polymer Chemistry an Introduction 1975
Addison-Wesley Publishing Company
43. Brauer G. M. and Davenport R. M., "Accelerating Effect of
Amines on Polymerization of Methyl Methacrylate"
Morden Plastics 153-168 1956
44. Dostal H. "A Basis for the Reaction Kinetics of Mixed
Polymerization" Monatsh 69 424-426 1936

45. Turner A. J., and Charles C.P., "Relative Reactivities in Vinyl Copolymerization" J. Polymer Sci. 2, 101-106 1947
46. Mayo F. R., and Walling C., "copolymerization " Chem. Revs. 46, 191-287 1950
47. Simha R., and Branson H. , "Theory of Chain Copolymerization Reactions " J. Chem. Phys. 12: 253-267 1944
48. Walling C., "Copolymerization XIII. Over-All Rates in Copolymerization Polar Effects in chain Initiation and Termination " J.Amer. Chem. Soc. 71: 1930-1935 1949
49. Wolff E. M. " The Effect of Cross-Linking Agents on Acrylic Resins" Aust. Dent. J., 7: 439-444 1962
50. Masuhara E., and Hirasawa R., " Studies of Reforming Dental Acrylic Resin (VII) of the Cross-Linked Polymethacrylate "Rep. RES. Inst. Den. Mat. , Tokyo Med. and Den. U., 1 (7) 77-84 1957
51. Caul H. J., and Sweeney W.T., "Relationship between Residual Monomer and some Properties of Self-Curing Dental Resin" J. Amer. Dent. Ass. 53: 60-63 1956
52. Sweeney W.T., and Sheenian W. D., "Mechanical Properties of Direct Filling Resins" J. Amer. Dent. Ass. 49 : 513-521 1954
53. Braden M., and Wright P. S., " Water Absorption and Water Solubility of Soft Lining Materials for Acrylic Dentures " J. Dent. Res. 62 (6) 764-768 June 1893